

TABLES OF MINERALS

INCLUDING THE
USES OF MINERALS
AND
STATISTICS OF THE DOMESTIC PRODUCTION


By S. L. PENFIELD

PROFESSOR OF MINERALOGY IN THE SHEFFIELD SCIENTIFIC SCHOOL
OF YALE UNIVERSITY

NEW HAVEN, CONN.

1903

2⁰⁰ 6/6/80
PLB CT

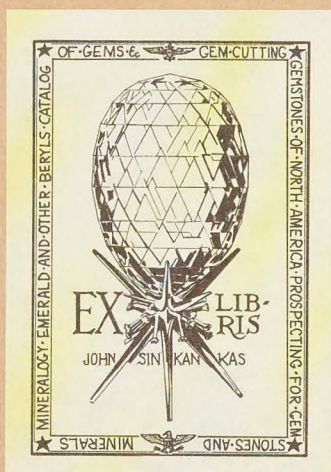

INTRODUCTION.

The minerals are arranged in the tables as follows :

I. According to the six systems of crystallization and their prominent subdivisions, the minerals of each subdivision being arranged in accordance with the chemical classification as adopted by Dana.

II. According to the elements, emphasis being given to minerals which are important from an economic standpoint.

III. With reference to geological occurrence and association.

Minerals are given three ranks in the tables, indicated by the type used in printing the names of the species, as follows:—

(1) Minerals of the first rank are either very common, or especially important from a scientific or geological standpoint, and their names are printed in heavy type, capital letters.

(2) Minerals which are of rather rare occurrence, including some very rare species provided they are especially important from an economic or scientific standpoint, are given a second rank, and their names are printed in heavy type, capital and small letters.

(3) The names of rarer and less important species, constituting a third rank, are printed in small type. All of the important minerals (450 species) are included in the tables, and generally very rare species have been omitted, except where chemical composition or some pronounced features have given them special significance. The weighting of the minerals, or assignment to first, second or third rank, is an arbitrary matter, based upon the writer's experience, but it is believed that students will appreciate this feature of the tables, enabling them almost at a glance to form some estimate of the relative importance of the several species.

Accompanying the names of the minerals their chemical formulas are given, and also numbers corresponding to pages in the *Text Book of Mineralogy, and System of Mineralogy* of Prof. E. S. Dana, where descriptions of the species may be found.

SYNOPSIS OF THE CHEMICAL CLASSIFICATION OF DANA.

1. **Native Elements.**
2. **Sulphides, Arsenides, Selenides, Tellurides.**
3. **Sulpharsenites, Sulphantimonites, Sulphobismuthites.**
4. **Chlorides, Bromides, Fluorides.**
5. **Oxides.**
6. **Carbonates.**
7. **Silicates, Titanates.**
8. **Niobates, Tantalates.**
9. **Phosphates, Arsenates, Vanadates.**
10. **Borates.**
11. **Uranates.**
12. **Sulphates, Chromates.**
13. **Tungstates, Molybdates.**

I. ARRANGEMENT OF MINERALS ACCORDING TO THE SIX SYSTEMS OF CRYSTALLIZATION.

NOTE.—The chief object of tables of this kind is that they may serve as a guide and reference-list to accompany lectures on crystallography and descriptive mineralogy. In a measure also the tables may be made the basis of determinative mineralogy, for if it is discovered that a mineral crystallizes in a certain system, the list of minerals in that system may be studied and the name of the species found by comparison either with labeled specimens or with descriptions as given in the texts referred to.

ISOMETRIC SYSTEM; NORMAL GROUP.

NOTE.—The pyritohedral and tetrahedral groups are tabulated separately, while a few minerals belonging to the rarer plagihedral division are included in the normal group.

Elements.

1.	DIAMOND , C (perhaps tetrahedral), ...	271, *3
2.	GOLD , Au, always with some Ag, ...	275, 14
3.	SILVER , Ag, ...	278, 19
4.	COPPER , Cu, ...	278, 20
5.	Platinum , Pt, ...	280, 25
6.	Iron , Fe with Ni, both terrestrial and meteoric, ...	281, 28

* See previous page, last paragraph.

Sulphides, Selenides, Tellurides.

1.	CALENA , Pb S, often carrying Ag.	287, 48
2.	Altaite, Pb Te,	288, 51
3.	Argentite , Ag ₂ S,	288, 46
4.	Hessite, Ag ₂ Te,	289, 47
5.	Petzite, (Ag, Au) ₂ Te,	289, 48
6.	Berzelianite, Cu ₂ Se,	289, 52
7.	Crookesite, (Cu, Tl, Ag) ₂ Se,	289, 54
8.	Pentlandite , (Ni, Fe) S,	293, 65
9.	BORNITE , Cu ₃ Fe S ₂ ,	297, 77
10.	Linnaeite , Co ₃ S ₄	297, 78
11.	Argyrodite, Ag ₈ Ge S ₆ = 4 Ag ₂ S. Ge S ₂ ,	316, 150
12.	Canfieldite, Ag ₈ Sn S ₆ = 4 Ag ₂ S. Sn S ₂ ,	316, —

Chlorides, Bromides, Fluorides.

1.	HALITE , Na Cl,	317, 154
2.	SYLVITE , K Cl (plagihedral),	318, 156
3.	Cerargyrite , Ag Cl,	319, 158
4.	Embolite , Ag (Cl, Br),	319, 159
5.	Nantokite, Cu Cl,	317, 154
6.	Percylite (Bolélite), Pb Cu Cl ₂ [OH] ₂ ,	322, 172
7.	FLUORITE , Ca F ₂ ,	320, 161
8.	Ralstonite (Na ₂ , Mg) F ₂ . 3 Al (F, OH) ₃ . 2H ₂ O,	323, 181

Oxides.

1.	Arsenolite, As ₂ O ₃ ,	330, 198
2.	Senarmontite , Sb ₂ O ₃ ,	330, 198
3.	CUPRITE , Cu ₂ O (plagihedral),	331, 206
4.	Periclase, Mg O,	331, 207
5.	Manganosite, Mn O,	332, 207
6.	SPINEL , Mg Al ₂ O ₄ , Fe iso. w. Mg,	338, 220
7.	Gahnite , Zn Al ₂ O ₄ , Fe and Mn iso. w. Zn,	339, 223
8.	MAGNETITE , Fe Fe ₂ O ₄ ,	339, 224
9.	Franklinite , (Fe, Mn, Zn) (Fe, Mn) ₂ O ₄ ,	341, 227
10.	CHROMITE , (Fe, Mn) Cr ₂ O ₄ ,	341, 228

Carbonates.

1. Northupite, $\text{Mg CO}_3 \cdot \text{Na}_2 \text{CO}_3 \cdot \text{Na Cl}$, . . . 364, —

Metasilicates.

1. **LEUCITE**, $\text{K Al [Si O}_3\text{]}_2$, . . . 381, 342
 2. **ANALCITE**, $\text{Na Al [Si O}_3\text{]}_2 \cdot \text{H}_2 \text{O}$, . . . 460, 595
 3. Pollucite, $\text{H}_2 \text{Cs}_4 \text{Al}_4 \text{[Si O}_3\text{]}_9$, . . . 382, 343

Orthosilicates.

1. **Sodalite**, $\text{Na}_4 \text{[Al Cl] Al}_2 \text{[Si O}_4\text{]}_3$, . . . 412, 429
 2. Häüynite, $[\text{Na}_2, \text{Ca}]_2 \text{[Al . Na SO}_4\text{] Al}_2 \text{[Si O}_4\text{]}_3$, . . . 412, 431
 3. **Lazurite**, $\text{Na}_4 \text{[Al . Na S}_3\text{] Al}_2 \text{[Si O}_4\text{]}_3$, . . . 413, 432

4. **GARNET**, $\left\{ \begin{array}{l} \text{Grossularite, Ca}_3 \text{Al}_2 \text{[Si O}_4\text{]}_3, \\ \text{Pyrope, Mg}_3 \text{Al}_2 \text{[Si O}_4\text{]}_3, \\ \text{Almandite, Fe}_3 \text{Al}_2 \text{[Si O}_4\text{]}_3, \\ \text{Spessartite, Mn}_3 \text{Al}_2 \text{[Si O}_4\text{]}_3, \\ \text{Andradite, Ca}_3 \text{Fe}_2 \text{[Si O}_4\text{]}_3, \\ \text{Uvarovite, Ca}_3 \text{(Cr, Al)}_2 \text{[Si O}_4\text{]}_3 \end{array} \right.$. . . 415, 437

Titanates, Manganates.

1. Perovskite, Ca Ti O_3 , . . . 487, 722
 2. Bixbyite, $\text{Fe Mn O}_3 = \text{Fe O} \cdot \text{Mn O}_2$, . . . 343, —

Niobates, Tantalates.

1. Pyrochlore, $\text{R Nb}_2 \text{O}_6 \cdot \text{R (Ti, Th) O}_3$, $\text{R} = \text{Ca and Na}_2$, . . . 489, 726
 2. Microlite, $\text{Ca}_2 \text{Ta}_2 \text{O}_7$, . . . 489, 728

Uranates.

1. **Uraninite**, UO_3 and UO_2 , with Th, Y, Ce, Pb, He? 521, 889

Sulphates.

1. Sulphohalite, $2 \text{Na}_2 \text{SO}_4 \cdot \text{Na Cl} \cdot \text{Na F}$, . . . 530, 917

ISOMETRIC SYSTEM; PYRITOHEDRAL GROUP.

Sulphides, Arsenides, Antimonides.

1.	PYRITE , Fe S_2 ,		300, 84
2.	Hauerite, Mn S_2 ,		301, 87
3.	Smaltite , Co As_2 ,		301, 87
4.	Chloanthite , Ni As_2 ,		301, 87
5.	Cobaltite , Co As S ,		301, 89
6.	Cersdorffite , Ni As S ,		302, 90
7.	Ullmannite, Ni Sb S ,		302, 91
8.	Sperryllite, Pt As_2 ,		302, 92

Sulphates.

1.	Kalinite, Alum , $\text{K Al [SO}_4\text{]}_2 \cdot 12 \text{ H}_2\text{O}$,		535, 951
----	--	-----------	----------

ISOMETRIC SYSTEM; TETRAHEDRAL GROUP.

Sulphides, Selenides.

1.	SPHALERITE , Zn S , with isomorphous Fe and Cd,		291, 59
2.	Tiemannite , Hg Se , S iso. w. Se,		292, 63
3.	Onofrite, Hg (S, Se) ,		292, 64
4.	Alabandite , Mn S ,		292, 64

Sulphantimonites, Sulpharsenites.

1.	TETRAHEDRITE , $\text{Cu}_8 \text{Sb}_2 \text{S}_7 = 4 \text{ Cu}_2 \text{S} \cdot \text{Sb}_2 \text{S}_3$,	312, 137
2.	TENNANTITE , $\text{Cu}_8 \text{As}_2 \text{S}_7 = 4 \text{ Cu}_2 \text{S} \cdot \text{As}_2 \text{S}_3$,	313, 137

Chlorides, Bromides, Iodides.

1.	Marshite, Cu I ,		317, —
2.	Miersite, $4 \text{ Ag I} \cdot \text{Cu I}$,		319, —

Orthosilicates.

1.	Helvite, $(\text{Mn, Fe})_2 (\text{Mn}_2 \text{S}) \text{Be}_3 [\text{Si O}_4]_3$,		414, 434
2.	Eulytite, $\text{Bi}_4 [\text{Si O}_4]_3$,		414, 436
3.	Zunytite, $[\text{Al} \cdot 2 (\text{OH, F, Cl})]_6 \text{Al}_2 [\text{Si O}_4]_3$,		414, 436

Phosphates, Arsenates.

1.	Pharmacosiderite, $\text{Fe [Fe} \cdot \text{OH]}_3 [\text{As O}_4]_3 \cdot 6 \text{ H}_2\text{O}$,		513, 847
----	--	-----------	----------

Borates.

1.	Boracite , $\text{Mg}_7 \text{Cl}_2 \text{B}_{16} \text{O}_{30}$,		519, 879
----	---	-----------	----------

TETRAGONAL SYSTEM; NORMAL GROUP.

Sulphides.

1. **Stannite**, $\text{Cu}_2 \text{Fe Sn S}_4 = \text{Cu}_2 \text{S} \cdot \text{FeS} \cdot \text{SnS}_2$, . 315, 83

Chlorides.

1. Calomel, Hg Cl_2 , ... 317, 153
2. Matlockite, $\text{Pb}_2 \text{O Cl}_2$, ... 322, 169

Oxides, and closely related Silicates and Phosphates.

1. Hausmannite, $\text{Mn}_3 \text{O}_4$, ... 342, 230
2. Braunite, Mn Mn O_3 , with Mn Si O_3 , ... 343, 232
3. **Octadecrite**, Ti O_2 , ... 346, 240
4. **CASSITERITE**, Sn O_2 or Sn Sn O_4 , ... 344, 234
5. **RUTILE**, Ti O_2 or Ti Ti O_4 , ... 345, 237
6. Polianite, Mn O_2 or Mn Mn O_4 , ... 345, 236
7. Plattnerite, Pb O_2 or Pb Pb O_4 , ... 346, 239
8. **ZIRCON**, Zr Si O_4 , ... 429, 482
9. **Thorite**, Th Si O_4 , ... 430, 488
10. **Xenotime**, Y P O_4 , ... 494, 748

Carbonates.

1. **Phosgenite**, $[\text{Pb Cl}]_2 \text{CO}_3$, ... 364, 292

Silicates.

1. Hardystonite, $\text{Ca}_2 \text{Zn Si}_2 \text{O}_7$, ... Appendix 32
2. Ganomalite, $\text{Pb}_4 [\text{Pb} \cdot \text{OH}]_2 \text{Ca}_4 [\text{Si}_2 \text{O}_7]_3$, ... 408, 422
3. Nasonite, $\text{Pb}_4 [\text{Pb Cl}]_2 \text{Ca}_4 [\text{Si}_2 \text{O}_7]_3$, ... Appendix 48
4. **Mellilite**, Complex Ca, Mg, Na, Al, Fe silicate, ... 426, 474
5. **VESUVIANITE**, Complex Ca, Al silicate, ... 427, 477
6. **Apophyllite**, $\text{H}_7 \text{K Ca}_4 [\text{Si O}_3]_8 \cdot 4\frac{1}{2} \text{H}_2\text{O}$, ... 452, 566

Niobates, Tantalates.

1. Tapiolite, $\text{Fe (Ta, Nb)}_2 \text{O}_6$, ... 492, 738

Phosphates, Arsenates.

1. Torbernite, $\text{Cu [U O}_2\text{]}_2 [\text{P O}_4\text{]}_2 \cdot 8 \text{H}_2\text{O}$, ... 515, 856
2. Zeunerite, $\text{Cu [U O}_2\text{]}_2 [\text{As O}_4\text{]}_2 \cdot 8 \text{H}_2\text{O}$, ... 515, 857

TETRAGONAL SYSTEM; TRI-PYRAMIDAL GROUP.

Silicates.

1. **WERNERITE**, or $\left\{ \begin{array}{l} \text{Ca}_4 \text{Al}_6 \text{Si}_6 \text{O}_{26} \text{ with } \\ \text{Na}_4 \text{Al}_3 \text{Si}_9 \text{O}_{24} \text{Cl,} \end{array} \right\}$. . . 425, 468
-

Niobates, Tantalates.

1. Fergusonite, R (Nb, Ta) O_4 , $\text{R} = \text{Y, Er, Ce}$, . . . 490, 729
-

Tungstates, Molybdates.

1. **Scheelite**, Ca W O_4 , ... 540, 985
 2. Stolzite, Pb W O_4 , ... 541, 989
 3. **Wulfenite**, Pb Mo O_4 , ... 541, 989
-

TETRAGONAL SYSTEM; SPHENOIDAL GROUP.

Sulphides.

1. **CHALCOPYRITE**, Cu Fe S_2 , ... 297, 80
-

Silicates.

1. Edingtonite, $\text{Ba Al}_2 \text{Si}_3 \text{O}_{10} \cdot 3 \text{H}_2 \text{O}$, ... 460, 599
-

HEXAGONAL SYSTEM ; NORMAL GROUP.

Elements.

1. Iridosmine, Ir with Os, ... 280, 27

Sulphides.

1. **Molybdenite**, Mo S_2 , ... 285, 41
2. Covellite, Cu S , ... 294, 68
3. **PYRRHOTITE**, $\text{Fe}_{11} \text{S}_{12}$ (Fe S ?), ... 296, 73

Fluorides.

1. Tysonite, $(\text{Ce, La, Di}) \text{F}_3$, ... 321, 166

Oxides.

1. Tridymite, Si O_2 , ... 328, 192

Carbonates.

1. Parisite, $[\text{R F}]_2 \text{Ca} [\text{CO}_3]_3$, $\text{R} = \text{Ce, La, Di}$, ... 364, 290

Silicates.

1. **BERYL**, $\text{Be}_3 \text{Al}_2 [\text{Si O}_3]_6$, with some $[\text{OH}]?$ 405, 405
 2. Barysilite, $\text{Pb}_3 \text{Si}_2 \text{O}_7$, ... 408, 421
 3. **NEPHELITE**, approximately Na Al Si O_4 , ... 409, 423
 4. Encryptite, Li Al Si O_4 , ... 410, 426
 5. Cancrinite, $\text{H}_6 \text{Na}_6 \text{Ca} (\text{Na CO}_3) \text{Al}_8 [\text{Si O}_4]_9$, ... 411, 427
-
6. Pyrosmalite, $\text{H}_7 [\text{Fe Cl}] \text{Fe}_4 [\text{Si O}_4]_4$, Mn iso. w. Fe, ... 424, 465
 7. Fiedlerite, $\text{H}_7 [\text{Mn Cl}] \text{Mn}_4 [\text{Si O}_4]_4$, ... 424, 465
-
8. Thaumassite, $\text{Ca Si O}_3 \cdot \text{Ca CO}_3 \cdot \text{Ca SO}_4 \cdot 15 \text{H}_2\text{O}$, ... 483, 698

Sulphates.

1. Hanksite, $9 \text{Na}_2 \text{SO}_4 \cdot 2 \text{Na}_2 \text{CO}_3 \cdot \text{K Cl}$, ... 530, 920

HEXAGONAL SYSTEM; HEMIMOPHIC GROUP.

Sulphides, Arsenides, Antimonides.

1.	Greenockite , Cd S,		294, 69
2.	Wurtzite, Zn S,		295, 70
3.	Niccolite , Ni As,		295, 71
4.	Breithauptite, Ni Sb,		296, 72

Chlorides, Iodides.

1.	Iodyrite, Ag I,		319, 160
----	-----------------	-----------	----------

Oxides.

1.	Zincite , Zn O, with Mn O,		332, 208
----	-----------------------------------	-----------	----------

HEXAGONAL SYSTEM; TRI-PYRAMIDAL GROUP.

Phosphates, Arsenates, Vanadates.

1.	APATITE ,	Ca ₄ [Ca F] [PO ₄] ₃ ,		497, 762
2.	PYROMORPHITE ,	Pb ₄ [Pb Cl] [PO ₄] ₃ ,		499, 770
3.	Mimetite ,	Pb ₄ [Pb Cl] [As O ₄] ₃ ,		500, 771
4.	Vanadinite ,	Pb ₄ [Pb Cl] [VO ₄] ₃ ,		500, 773

 HEXAGONAL-RHOMBOHEDRAL SYSTEM;
NORMAL GROUP.

NOTE.—A few hemimorphic species are included in the tables with the *Normal Group*. The *Tri-Rhombohedral* and *Trapezohedral* groups are in separate tables.

Elements.

1.	GRAPHITE , C,		273, 7
2.	Arsenic , As,		274, 11
3.	Antimony , Sb,		275, 12
4.	Bismuth , Bi,		275, 13
5.	Tellurium, Te,		275, 11

Sulphides, Tellurides.

1.	Tetradymite, Bi ₂ Te ₂ S,		284, 39
2.	Millerite , Ni S,		295, 70

Sulphantimonites, Sulpharsenites.

1.	Pyrargyrite , Ag ₃ Sb S ₃ or 3 Ag ₂ S . Sb ₂ S ₃ ,		311, 131
2.	Proustite , Ag ₃ As S ₃ or 3 Ag ₂ S . As ₂ S ₃ ,		311, 134

Oxides, Hydroxides.

1. **CORUNDUM**, Al_2O_3 , ... 333, 210
2. **HEMATITE**, Fe_2O_3 , ... 334, 213
Ilmenite, see tri-rhombohedral group.
3. **Brucite**, $\text{Mg}[\text{OH}]_2$, ... 351, 252
4. **Pyrochroite**, $\text{Mn}[\text{OH}]_2$, ... 351, 253
5. **Chalcophanite**, $(\text{Zn}, \text{Fe})\text{Mn}_2\text{O}_5 \cdot 2\text{H}_2\text{O}$, ... 352, 265

Carbonates.

1. **CALCITE**, CaCO_3 , ... 354, 262
Dolomite, see tri-rhombohedral group.
2. **Magnesite**, MgCO_3 , ... 358, 274
3. **SIDERITE**, FeCO_3 , ... 359, 276
4. **RHODOCHROSITE**, MnCO_3 , ... 359, 278
5. **SMITHSONITE**, ZnCO_3 , ... 360, 279

Silicates.

1. **Eudialyte**, $\text{Na}_{18}(\text{Ca}, \text{Fe})_6\text{Cl}(\text{Si}, \text{Zr})_{20}\text{O}_{52}?$ 407, 409
2. **TOURMALINE**, $\text{R}_9\text{Al}_3[\text{B} \cdot \text{OH}]_2\text{Si}_4\text{O}_{19}$ (hemi-morphic), ... 447, 551
3. **Chabazite**, $(\text{Ca}, \text{Na}_2)\text{Al}_2\text{Si}_4\text{O}_{12} \cdot 6\text{H}_2\text{O}?$ 458, 589
4. **Gmelinite**, $(\text{Na}_2\text{Ca})\text{Al}_2\text{Si}_4\text{O}_{12} \cdot 6\text{H}_2\text{O}?$ 459, 593
5. **Penninite**, $\text{H}_8(\text{Mg}, \text{Fe})_5\text{Al}_2\text{Si}_3\text{O}_{18}$, ... 474, 650

Phosphates, Arsenates.

1. **Hamlinite**, $[\text{Al} \cdot 2\text{OH}]_3[\text{Sr} \cdot \text{OH}]\text{P}_2\text{O}_7$, ... 503, 762
2. **Chalcophyllite**, $[\text{Cu} \cdot \text{OH}]_3\text{AsO}_4 \cdot \text{Cu}[\text{OH}]_2 \cdot 3\frac{1}{2}\text{H}_2\text{O}$, 511, 840

Nitrates.

1. **SODA-NITER**, NaNO_3 (homœomorphous with CaCO_3), ... 517, 870

Sulphates.

1. **Spangolite**, $\text{Cu}_6\text{AlClSO}_{10} \cdot 9\text{H}_2\text{O}$ (hemimorphic), ... 530, 919
2. **Alunite**, $\text{K}_2[\text{Al} \cdot 2\text{OH}]_6[\text{SO}_4]_4$, Na iso. w. K, ... 537, 974
3. **Jarosite**, $\text{K}_2[\text{Fe} \cdot 2\text{OH}]_6[\text{SO}_4]_4$, ... 537, 974
4. **Natrojarosite**, $\text{Na}_2[\text{Fe} \cdot 2\text{OH}]_6[\text{SO}_4]_4$, ... —, —
5. **Plumbojarosite**, $\text{Pb}[\text{Fe} \cdot 2\text{OH}]_6[\text{SO}_4]_4$, ... —, —

HEXAGONAL-RHOMBOHEDRAL SYSTEM;
TRI-RHOMBOHEDRAL GROUP.

Titanates.

1. **Ilmenite**, $\text{Fe Ti O}_3 = \text{Fe O} \cdot \text{Ti O}_2$, Mg iso. w. Fe, 336, 217

Carbonates.

1. **DOLOMITE**, $\text{Ca Mg} [\text{CO}_3]_2$, Fe iso. w. Mg, 357, 271

Silicates.

1. **Willemite**, $\text{Zn}_2 \text{Si O}_4$, Mn iso. w. Zn, . . . 422, 460
 2. **Phenacite**, $\text{Be}_2 \text{Si O}_4$, ... 423, 462
 3. Diopside, $\text{H}_2 \text{Cu Si O}_4$, ... 424, 463

HEXAGONAL-RHOMBOHEDRAL SYSTEM;
TRAPEZOHEDRAL GROUP.

Sulphides.

1. **CINNABAR**, Hg S , ... 293, 66

Oxides.

1. **QUARTZ**, Si O_2 , ... 324, 183

ORTHORHOMBIC SYSTEM.

Elements.

1. **SULPHUR**, S, ... 273, 8

Sulphides, Arsenides, Antimonides, Tellurides.

1. **STIBNITE**, $\text{Sb}_2 \text{S}_3$, ... 283, 36
2. **Bismuthinite**, $\text{Bi}_2 \text{S}_3$, ... 284, 38
3. **CHALCOCITE**, $\text{Cu}_2 \text{S}$, ... 290, 55
4. **Stromeyerite**, Cu Ag S , or $\text{Cu}_2 \text{S} \cdot \text{Ag}_2 \text{S}$, ... 290, 56
5. **MARCASITE**, Fe S_2 , ... 302, 94
6. **Löllingite**, Fe As_2 , ... 303, 96
7. **ARSENOPYRITE**, Fe S As , or $\text{Fe S}_2 \cdot \text{Fe As}_2$, ... 303, 97
8. **Safflorite**, Co As_2 , ... 304, 100
9. **Rammelsbergite**, Ni As_2 , ... 304, 101
10. **Glaucodot**, $(\text{Co, Fe}) \text{S As}$, ... 304, 101
11. **Alloclasite**, Co S (As, Bi) , ... 304, 102
12. **Wolfachite**, Ni S (As Sb) , ... 304, 102
13. **Krennerite**, Au Te_2 , Ag iso. w. Au , ... 305, 105

Sulphantimonites, Sulpharsenites, Sulphobismuthites.

1. **Zinkenite**, $\text{Pb Sb}_2 \text{S}_4 = \text{Pb S} \cdot \text{Sb}_2 \text{S}_3$, ... 307, 112
2. **Sartorite**, $\text{Pb As}_2 \text{S}_4 = \text{Pb S} \cdot \text{As}_2 \text{S}_3$, ... 308, 112
3. **Emplectite**, $\text{Cu}_2 \text{Bi}_2 \text{S}_4 = \text{Cu}_2 \text{S} \cdot \text{Bi}_2 \text{S}_3$, ... 308, 113
4. **Chalcostibite**, $\text{Cu}_2 \text{Sb}_2 \text{S}_4 = \text{Cu}_2 \text{S} \cdot \text{Sb}_2 \text{S}_3$, ... 308, 113
5. **Galenobismuthite**, $\text{Pb Bi}_2 \text{S}_4 = \text{Pb S} \cdot \text{Bi}_2 \text{S}_3$, ... 308, 114
6. **Berthierite**, $\text{Fe Sb}_2 \text{S}_4 = \text{Fe S} \cdot \text{Sb}_2 \text{S}_3$, ... 308, 114
7. **Matildite**, $\text{Ag}_2 \text{Bi}_2 \text{S}_4 = \text{Ag}_2 \text{S} \cdot \text{Bi}_2 \text{S}_3$, ... 308, 115
8. **Cosalite**, $\text{Pb}_2 \text{Bi}_2 \text{S}_6 = 2 \text{Pb S} \cdot \text{Bi}_2 \text{S}_3$, ... 309, 121
9. **Jamesonite**, $\text{Pb}_2 \text{Sb}_2 \text{S}_6 = 2 \text{Pb S} \cdot \text{Sb}_2 \text{S}_3$, ... 308, 122
10. **Bournonite**, $(\text{Pb, Cu}_2)_3 \text{Sb}_2 \text{S}_6$ or $3 (\text{Pb, Cu}_2) \text{S} \cdot \text{Sb}_2 \text{S}_3$, ... 310, 126
11. **Wittichenite**, $\text{Cu}_3 \text{Bi S}_3$ or $3 \text{Cu}_2 \text{S} \cdot \text{Bi}_2 \text{S}_3$, ... 310, 128
12. **Aikinite**, $(\text{Pb, Cu}_2)_3 \text{Bi}_2 \text{S}_6 = 3 (\text{Pb, Cu}_2) \text{S} \cdot \text{Bi}_2 \text{S}_3$, ... 310, 129
13. **Meneghinite**, $\text{Pb}_4 \text{Sb}_2 \text{S}_7 = 4 \text{Pb S} \cdot \text{Sb}_2 \text{S}_3$, ... 313, 142
14. **Geocronite**, $\text{Pb}_6 \text{Sb}_2 \text{S}_8$ or $5 \text{Pb S} \cdot \text{Sb}_2 \text{S}_3$, ... 314, 143
15. **Stephanite**, $\text{Ag}_5 \text{Sb S}_4$ or $5 \text{Ag}_2 \text{S} \cdot \text{Sb}_2 \text{S}_3$, ... 314, 143

Sulpharsenates, Sulphantimonates.

1. **Enargite**, $\text{Cu}_3 \text{AsS}_4$ or $3 \text{Cu}_2 \text{S} \cdot \text{As}_2 \text{S}_5$, . . . 315, 147
2. **Famatinite**, $\text{Cu}_3 \text{SbS}_4$ or $3 \text{Cu}_2 \text{S} \cdot \text{Sb}_2 \text{S}_5$, . . . 315, 149

Chlorides.

1. **Cotunnite**, PbCl_2 , ... 321, 165
2. **Atacamite**, $\text{Cu}_2 \text{Cl} [\text{OH}]_3$, ... 322, 172
3. **Carnallite**, $\text{K Mg Cl}_3 \cdot 6 \text{H}_2\text{O}$, ... 323, 177

Oxides, Hydroxides.

1. **Valentinite**, $\text{Sb}_2 \text{O}_3$, ... 330, 199
2. **Chrysoberyl**, $\text{Be Al}_2 \text{O}_4$, ... 342, 229
3. **Brookite**, TiO_2 , ... 347, 242
4. **Diaspore**, $\text{Al}_2 \text{O}_3 [\text{OH}]_2$, ... 348, 246
5. **COETHITE**, $\text{Fe}_2 \text{O}_3 [\text{OH}]_2$, ... 349, 247
6. **MANGANITE**, $\text{Mn}_2 \text{O}_3 [\text{OH}]_2$, ... 349, 248
7. **PYROLUSITE**, MnO_2 with about 2% H_2O (pseudomorphous), ... 347, 243

Carbonates.

1. **ARAGONITE**, CaCO_3 , ... 361, 281
 2. **STRONTIANITE**, SrCO_3 , ... 362, 285
 3. **WITHERITE**, BaCO_3 , ... 362, 284
 4. **CERUSSITE**, PbCO_3 , ... 363, 286
-
5. **Nesquehonite**, $\text{MgCO}_3 \cdot 3 \text{H}_2\text{O}$, ... 366, 300
 6. **Pirssonite**, $\text{CaCO}_3 \cdot \text{Na}_2 \text{CO}_3 \cdot 2 \text{H}_2\text{O}$ (hemimorphic), 366, 303
 7. **Lanthanite**, $\text{La}_2 [\text{CO}_3]_3 \cdot 9 \text{H}_2\text{O}$, ... 366, 302

Metasilicates.

1. **Enstatite**, MgSiO_3 , ... 384, 346
 2. **Bronzite - Hypersthene**, $(\text{Mg, Fe}) \text{SiO}_3$, . . . 385, 348
-
3. **Anthophyllite**, $(\text{Mg, Fe}) \text{SiO}_3$, ... 398, 384
 4. **Leucophanite**, $\text{Na} [\text{BeF}] \text{Ca} [\text{SiO}_3]_2$, . . . 407, 417

Mesosilicates.

1. **Iolite**, $(\text{Mg, Fe})_4 \text{Al}_6 [\text{Al} \cdot \text{OH}]_2 [\text{Si}_2 \text{O}_7]_{10}$, . . . 407, 419

Orthosilicates or Orthosilicate Derivatives.

1. Monticellite, Ca Mg Si O_4 , ... 422, 449
 2. Glaucocroite, Ca Mn Si O_4 , ... Ap. 29
 3. Forsterite, $\text{Mg}_2 \text{ Si O}_4$, ... 422, 450
 4. **CHRYSLITE or OLIVINE**, $(\text{Mg, Fe})_2 \text{ Si O}_4$, 420, 451
 5. Fayalite, $\text{Fe}_2 \text{ Si O}_4$, ... 422, 456
 6. Tephroite, $\text{Mn}_2 \text{ Si O}_4$, ... 422, 457
-
7. **Danburite**, $\text{Ca B}_2 [\text{Si O}_4]_2$, ... 431, 490
 8. **TOPAZ**, $[\text{Al F}]_2 \text{ Si O}_4$ with isomorphous $[\text{Al. OH}]_2 \text{ Si O}_4$, ... 431, 492
 9. **Andalusite**, $[\text{Al O}] \text{ Al Si O}_4$, ... 432, 496
 10. **Zoisite**, $\text{Ca}_2 [\text{Al. OH}] \text{ Al}_2 [\text{Si O}_4]_3$, ... 437, 513
 11. **Prehnite**, $\text{H}_2 \text{ Ca}_2 \text{ Al}_2 [\text{Si O}_4]_3$, ... 442, 529
 12. Humite, $[\text{Mg (F, OH)}]_2 \text{ Mg}_5 [\text{Si O}_4]_3$, ... 443, 535
 13. Ilvaite, $\text{Ca Fe}_2 [\text{Fe. OH}] [\text{Si O}_4]_2$, ... 445, 541
-
14. Kentrolite, $[\text{Mn}_4 \text{ O}_8] \text{ Pb}_3 [\text{Si O}_4]_3$, ... 446, 544
 15. Melanotekite, $[\text{Fe}_4 \text{ O}_8] \text{ Pb}_3 [\text{Si O}_4]_3$, ... 446, 545
-
16. **CALAMINE**, $\text{H}_2 [\text{Zn}_2 \text{ O}] \text{ Si O}_4$ (hemimorphic), ... 446, 547
 17. Dumortierite, $\text{Al}_4 [\text{Al O}]_{16} [\text{Si O}_4]_7$, H_3 and B iso. w. Al, 449, 558
 18. **STAUROLITE**, $(\text{Mg, Fe}) [\text{Al. OH}] [\text{Al O}]_4 [\text{Si O}_4]_2$, 450, 558

Miscellaneous Silicates.

1. **Sillimanite**, $\text{Al}_2 \text{ Si O}_5$ (compare Andalusite), ... 433, 498
2. Bertrandite, $\text{H}_2 \text{ Be}_4 \text{ Si}_2 \text{ O}_9$ (hemimorphic), ... 446, 545
3. Ardeninite, $\text{H}_{10} \text{ Mn}_{10} \text{ Al}_{10} \text{ V}_2 \text{ Si}_{10} \text{ O}_{55} ?$ 445, 542
4. Cerite, $\text{H}_6 \text{ Ce}_4 \text{ Si}_3 \text{ O}_{15} ?$ 447, 550

Hydrated Silicates.

1. **NATROLITE**, $\text{Na}_2 \text{ Al}_2 \text{ Si}_3 \text{ O}_{10} \cdot 2 \text{ H}_2 \text{ O}$, ... 461, 600
2. **Thomsonite**, $(\text{Na}_2, \text{Ca}) \text{ Al}_2 [\text{Si O}_4]_2 \cdot 2\frac{1}{2} \text{ H}_2 \text{ O}$, ... 462, 607

Niobates, Tantalates.

1. **COLUMBITE**, $(\text{Fe, Mn}) (\text{Nb, Ta})_2 \text{ O}_6$, ... 490, 731
2. Yttrotantalite, $(\text{Fe, Ca}) (\text{Y, Er, Ce})_2 (\text{Ta, Nb})_4 \text{ O}_{15} \cdot 4 \text{ H}_2 \text{ O}$, ... 492, 738
3. Samarskite, $(\text{Fe, UO}_2)_3 (\text{Y, Er, Ce})_2 (\text{Nb, Ta})_6 \text{ O}_{21}$, ... 492, 739
4. Aeschynite, $\text{R}_3 \text{ Nb}_4 \text{ O}_{13} \cdot \text{R}_2 (\text{Th, Ti})_5 \text{ O}_{13}$, $\text{R}=\text{Ce, La, Di, Y}$, ... 493, 742
5. Polynignite, $\text{Nb, Zr, Ti, Th, Ce, La, Di, Y, Fe, Ca}$, ... 493, 743
6. Euxenite, $\text{Nb, Ti, Y, Er, Ce, UO}_2, \text{Fe, H}$, ... 493, 744
7. Polycrase, $\text{Nb, Ti, Y, Er, Ce, UO}_2, \text{Fe, H}$, ... 493, 744

Phosphates, Arsenates, Vanadates.

1.	Pucherite, Bi VO_4 , ...	496, 755
2.	Triphylite , Li Fe PO_4 , Mn iso. w. Fe, ...	496, 756
3.	Lithiophilite , Li Mn PO_4 , Fe iso. w. Mn, ...	496, 756
4.	Natrophilite, Na Mn PO_4 , ...	496, 758
5.	Beryllonite, NaBe PO_4 , ...	496, 758
6.	Olivenite , $\text{Cu [Cu . OH] As O}_4$, ...	504, 784
7.	Libethenite, Cu [Cu . OH] PO_4 , ...	507, 786
8.	Adamite, $\text{Zn [Zn . OH] As O}_4$, ...	505, 786
9.	Descloizite, R [R . OH] VO_4 , R=Pb and Zn, ...	505, 787
10.	Dufrenite, $\text{Fe}_2 [\text{OH}]_3 \text{PO}_4$, ...	506, 797
11.	Struvite, $\text{NH}_4 \text{Mg PO}_4 \cdot 6 \text{H}_2\text{O}$ (hemimorphic), ...	507, 806
12.	Reddingite, $\text{Mn}_3 [\text{PO}_4]_2 \cdot 3 \text{H}_2\text{O}$, ...	508, 813
13.	Scorodite , $\text{Fe As O}_4 \cdot 2 \text{H}_2\text{O}$, ...	509, 821
14.	Strengite, $\text{Fe PO}_4 \cdot 2 \text{H}_2\text{O}$, ...	510, 822
15.	Euchroite, $\text{Cu}_2 [\text{Cu . OH}]_2 [\text{As O}_4]_2 \cdot 6 \text{H}_2\text{O}$, ...	511, 838
16.	Wavellite , $[\text{Al . OH}]_3 [\text{PO}_4]_2 \cdot 5 \text{H}_2\text{O}$, ...	512, 842
17.	Childrenite, $(\text{Fe, Mn}) [\text{Al O}] \text{PO}_4 \cdot 2 \text{H}_2\text{O}$, ...	513, 850
18.	Autunnite, $\text{Ca [UO}_2]_2 [\text{PO}_4]_2 \cdot 8 \text{H}_2\text{O}$, ...	515, 857

Nitrates.

1.	Niter , K N O_3 , ...	517, 871
2.	Gerhardtite, $\text{Cu}_4 [\text{OH}]_6 [\text{NO}_3]_2$, ...	517, 872

Borates.

1.	Sussexite, $\text{H (Mn, Mg, Zn) BO}_3$, ...	518, 876
2.	Ludwigite, $3 \text{Mg O} \cdot \text{B}_2\text{O}_3 + \text{Fe O} \cdot \text{Fe}_2\text{O}_3$, ...	518, 877
3.	Hambergite, Be [Be . OH] BO_3 , ...	518, 878
4.	Warwickite, $\text{Fe Mg}_6 \text{Ti}_2 \text{B}_6 \text{O}_{20}?$	519, 881
5.	Howlite, $\text{H}_5 \text{Ca}_2 \text{B}_5 \text{Si O}_{14}$, ...	519, 881

Sulphates.

1.	Thenardite, $\text{Na}_2 \text{S O}_4$,	.	.	.	.	.	.	523, 895
2.	BARITE , Ba SO_4 ,	.	.	.	.	.	.	524, 899
3.	CELESTITE , Sr SO_4 ,	.	.	.	.	.	.	526, 905
4.	ANCLESITE , Pb SO_4 ,	.	.	.	.	.	.	527, 907
5.	ANHYDRITE , Ca SO_4 ,	.	.	.	.	.	.	528, 910
6.	Brochantite , $\text{Cu}_4 [\text{OH}]_6 \text{SO}_4$,	.	.	.	.	.	.	530, 925
7.	Epsomite, $\text{Mg SO}_4 \cdot 7 \text{H}_2\text{O}$ (sphenoidal),	.	.	.	.	.	.	533, 938
8.	Goslarite, $\text{Zn SO}_4 \cdot 7 \text{H}_2\text{O}$ (sphenoidal),	.	.	.	.	.	.	533, 939
9.	Morenosite, $\text{Ni SO}_4 \cdot 7 \text{H}_2\text{O}$ (sphenoidal),	.	.	.	.	.	.	533, 940

MONOCLINIC SYSTEM.

NOTE.—With rare exceptions the minerals of this system all crystallize in the normal group.

Sulphides, Tellurides.

1. **Realgar**, As S_2 , ... 282, 33
 2. **Orpiment**, $\text{As}_2 \text{S}_3$, ... 282, 35
-
3. **Sylvanite**, Au Ag Te_2 , ... 304, 103
 4. **Calaverite**, Au Te_2 , with Ag iso. w. Au, . . . 305, 105

Sulphantimonites, Sulpharsenites.

1. Miargyrite, $\text{Ag}_2 \text{Sb}_2 \text{S}_4$ or $\text{Ag}_2 \text{S}$, $\text{Sb}_2 \text{S}_3$, . . . 308, 116
 2. Plagionite, $5 \text{ Pb S} \cdot 4 \text{ Sb}_2 \text{S}_3$, ... 308, 118
 3. Baumhauerite, $4 \text{ Pb S} \cdot 3 \text{ As}_2 \text{S}_3$, ... New species
 4. Dufrenoyite, $\text{Pb}_2 \text{As}_2 \text{S}_5$ or $2 \text{ Pb S} \cdot \text{As}_2 \text{S}_3$, . . 309, 120
 5. Freieslebenite, $(\text{Pb}, \text{Ag})_5 \text{Sb}_4 \text{S}_{11}$, ... 309, 124
 6. Jordanite, $\text{Pb}_4 \text{As}_2 \text{S}_7$ or $4 \text{ Pb S} \cdot \text{As}_2 \text{S}_3$, . . . 313, 141
-
7. **Polybasite**, $\text{Ag}_9 \text{Sb S}_6$, with Cu iso. w. Ag, . . . 314, 146
 8. Pearceite, $\text{Ag}_9 \text{As S}_6$, with Cu iso. w. Ag, . . . 315,

Fluorides.

1. **CRYOLITE**, $\text{Na}_3 \text{Al F}_6$, ... 321, 166
2. Pachnolite, $\text{Na Ca Al F}_6 \cdot \text{H}_2\text{O}$, ... 323, 179
3. Thomsenolite, $\text{Na Ca Al F}_6 \cdot \text{H}_2\text{O}$, ... 323, 180

Hydroxides.

1. **Gibbsite**, $\text{Al} [\text{OH}]_3$, ... 351, 254

Carbonates.

1. Barytocalcite, $\text{Ba Ca} [\text{CO}_3]_2$, ... 364, 289
2. **MALACHITE**, $[\text{Cu} \cdot \text{OH}]_2 \text{CO}_3$, ... 364, 294
3. **AZURITE**, $\text{Cu} [\text{Cu} \cdot \text{OH}]_2 [\text{CO}_3]_2$, ... 365, 295
4. **Aurichalcite**, $2 (\text{Zn}, \text{Cu}) \text{CO}_3 \cdot 3 (\text{Zn}, \text{Cu}) [\text{OH}]_2$, 366, 298
5. Leadhillite, $\text{Pb} [\text{Pb} \cdot \text{OH}]_2 \text{SO}_4 [\text{CO}_3]_2$, . . . 529, 921
6. Dawsonite, $\text{Na} [\text{Al} \cdot 2 \text{OH}] \text{CO}_3$, ... 366, 299
7. Natron, $\text{Na}_2 \text{CO}_3 \cdot 10 \text{H}_2\text{O}$, ... 366, 301
8. **Gay-Lussite**, $\text{Na}_2 \text{CO}_3 \cdot \text{Ca CO}_3 \cdot 5 \text{H}_2\text{O}$, . . . 366, 301
9. Trona, $\text{Na}_2 \text{CO}_3 \cdot \text{H Na CO}_3 \cdot 2 \text{H}_2\text{O}$, ... 367, 303
10. Hydromagnesite, $3 \text{Mg CO}_3 \cdot \text{Mg} [\text{OH}]_2 \cdot 3 \text{H}_2\text{O}$, . . 367, 304

Tetrasilicates.

1. Petalite, $\text{Li Al Si}_4 \text{O}_{10}$, ... 369, 311

Trisilicates.

1. Eudidymite, $\text{H Na Be Si}_3 \text{O}_8$, ... 369, 313
2. **ORTHOCLASE**, $\text{K Al Si}_3 \text{O}_8$, ... 369, 315
3. Hyalophane, $2 \text{ K Al Si}_3 \text{O}_8 \cdot \text{Ba Al}_3 \text{Si}_2 \text{O}_8$, ... 373, 322

Metasilicates.

1. **PYROXENE**, variety Diopside, $\text{Ca Mg} [\text{Si O}_3]_2$, ... 387, 352
2. **PYROXENE**, ordinary, $\text{Ca (Mg, Fe)} [\text{Si O}_3]_2$, ... 387, 352
3. **PYROXENE**, variety Augite, R Si O_3 with $(\text{Al, Fe})_2 \text{O}_3$, $\text{R} = \text{Ca, Mg, Fe and Mn}$, ... 390, 358
4. **Ægirite**, Acmite, $\text{Na Fe} [\text{Si O}_3]_2$, ... 391, 364
5. **Jadeite**, $\text{Na Al} [\text{Si O}_3]_2$, ... 393, 369
6. **SPODUMENE**, $\text{Li Al} [\text{Si O}_3]_2$, Na iso. w. Li, ... 393, 366
7. **WOLLASTONITE**, Ca Si O_3 , ... 394, 371
8. **Pectolite**, $\text{H Na Ca}_2 [\text{Si O}_3]_3$, ... 395, 373
9. **AMPHIBOLE**, variety Tremolite, R Si O_3 , $\text{R} = \text{Mg and Ca}$, ... 399, 385
10. **AMPHIBOLE**, Hornblende, R Si O_3 , with $(\text{Fe, Al})_2 \text{O}_3$, $\text{R} = \text{Mg, Fe, Ca}$, ... 399, 385
11. Glaucophane, $\text{Na Fe} [\text{Si O}_3]_2$ with $(\text{Mg, Fe}) \text{Si O}_3$, ... 403, 399
12. Carpholite, $\text{Mn} [\text{Al} \cdot 2 \text{ OH}]_2 [\text{Si O}_3]_2$, ... 447, 549

Orthosilicate Derivatives.

1. **DATOLITE**, $\text{Ca} [\text{B} \cdot \text{OH}] \text{Si O}_4$, ... 435, 502
2. Homilite, $(\text{Ca, Fe})_3 [\text{BO}]_2 [\text{Si O}_4]_2$, ... 436, 505
3. Euclase, $\text{Be} [\text{Al} \cdot \text{OH}] \text{Si O}_4$, ... 436, 508
4. Gadolinite, $\text{Be}_2 \text{Fe} [\text{YO}]_2 [\text{Si O}_4]_2$, ... 436, 509
5. **EPIDOTE**, $\text{Ca}_2 [\text{Al} \cdot \text{OH}] \text{Al}_2 [\text{Si O}_4]_3$, Fe iso. w. Ca and Al, ... 438, 516
6. Piedmontite, $\text{Ca}_2 [\text{Al} \cdot \text{OH}] (\text{Al, Mn, Fe})_2 [\text{Si O}_4]_3$, ... 440, 521
7. **Allanite**, $\text{Ca}_2 [\text{Al} \cdot \text{OH}] (\text{Al, Fe, Ce, La, Di})_2 [\text{Si O}_4]_3$, ... 440, 522
8. Prolectite, $[\text{Mg (F, OH)}] \text{Mg} [\text{Si O}_4]$, ... 443, —
9. Chondrodite, $[\text{Mg (F, OH)}]_2 \text{Mg}_3 [\text{Si O}_4]_2$, ... 443, 536
- p.14 Humite, $[\text{Mg (F, OH)}]_2 \text{Mg}_5 [\text{Si O}_4]_3$, ... 443, 535
10. Clinohumite, $[\text{Mg (F, OH)}]_2 \text{Mg}_7 [\text{Si O}_4]_4$, ... 443, 538
11. Clinohedrite, $\text{H}_2 [\text{Ca Zn O}] \text{Si O}_4$ (Clinohedral), ... 447, —

Hydrated Silicates ; Zeolite Section.

1. **Heulandite**, $H_4 Ca Al_2 [Si O_3]_6 \cdot 3 H_2 O$, . . . 454, 574
2. **Brewsterite**, $H_4 (Sr, Ba, Ca) Al_2 [Si O_3]_6 \cdot 3 H_2 O$, . . . 454, 576
3. **Wellsite**, $(Ba, Ca, K_2) Al_2 Si_3 O_{10} \cdot 3 H_2 O$, . . . 455, —
4. **Phillipsite**, $(K_2, Ca) Al_2 Si_4 O_{12} \cdot 4 H_2 O$, . . . 455, 579
5. **Harmotome**, $(K_2, Ba) Al_2 Si_5 O_{14} \cdot 5 H_2 O$, . . . 456, 581
6. **STILBITE**, $(Na_2, Ca) Al_2 Si_6 O_{10} \cdot 6 H_2 O$, . . . 456, 583
7. **Laumontite**, $H_4 Ca Al_2 Si_4 O_{14} \cdot 2 H_2 O$, . . . 457, 587
8. **Scolecite**, $Ca Al_2 Si_3 O_{10} \cdot 3 H_2 O$, . . . 462, 604

Foliated, Micaceous Silicates.

NOTE.—The crystallization of some of the minerals in this section is uncertain.

1. **MUSCOVITE**, $H_2 K Al_3 [Si O_4]_3$, . . . 464, 614
2. **Paragonite**, $H_2 Na Al_3 [Si O_4]_3$, . . . 467, 623
3. **LEPIDOLITE**, $K Li [Al \cdot 2 (OH, F)] Al [Si O_3]_3$, . . . 467, 624
4. **BIOTITE**, $(H, K)_2 (Mg, Fe)_2 Al_2 [Si O_4]_3$, . . . 467, 627
5. **PHLOGOPITE**, $H_2 K Mg_3 Al [Si O_4]_3 ?$. . . 469, 632
6. **Lepidomelane**, $(H, K)_2 Fe_3 (Fe, Al)_4 [Si O_4]_5 ?$. . . 470, 634
7. **Roscoelite**, $H_8 K (Mg, Fe) (Al, V)_4 [Si O_3]_{12} ?$. . . 470, 635
8. **Margarite**, $H_2 Ca Al_4 Si_2 O_{12}$, . . . 470, 636
9. **Seybertite**, $H_3 (Mg, Ca)_5 Al_5 Si_2 O_{18}$, . . . 471, 638
10. **Chloritoid**, $H_2 (Fe, Mg) Al_2 Si O_7$, . . . 471, 640
11. **CLINOCHLORE**, Chlorite, $H_8 Mg_5 Al_2 Si_3 O_{18}$. . . 473, 644
12. **Vermiculite**, H, Mg, Al , silicates of uncertain composition, . . . 476, 664
13. **SERPENTINE**, $H_4 Mg_3 Si_2 O_9$, . . . 476, 669
14. **KAOLIN**, $H_4 Al_2 Si_2 O_9$, . . . 481, 685
15. **TALC**, $H_2 Mg_3 [Si O_3]_4$, . . . 479, 678
16. **Pyrophyllite**, $H_2 Al_2 [Si O_3]_4$, . . . 482, 691

Titanosilicates.

1. **TITANITE**, $Ca Ti Si O_6$, . . . 485, 712
2. **Astrophyllite**, $(Na, K)_4 (Fe, Mn)_4 Ti [Si O_4]_4$, . . . 487, 719

Phosphates, Arsenates.

1. **Monazite**, $(Ce, La, Di) PO_4$ with $Th Si O_4$, . . . 495, 749
2. **Herderite**, $Ca [Be \cdot OH] PO_4$, with F iso. w. OH , . . . 503, 760

3.	Wagnerite, $\text{Mg} [\text{Mg F}] \text{PO}_4$, ...	502, 775
4.	Triplite, $\text{R} [\text{R F}] \text{PO}_4$, $\text{R}=\text{Fe}$ and Mn , ...	502, 777
5.	Triplidite, $\text{R} [\text{R. OH}] \text{PO}_4$, $\text{R}=\text{Fe}$ and Mn , ...	502, 779
6.	Durangite, $\text{Na} [\text{Al F}] \text{As O}_4$, ...	503, 780
7.	Clinoclasite, $[\text{Cu. OH}]_3 \text{As O}_4$, ...	505, 795
8.	Lazulite , $\text{Mg} [\text{Al. OH}]_2 [\text{PO}_4]_2$, ...	506, 798
9.	Vivianite , $\text{Fe}_3 [\text{PO}_4]_2 \cdot 8 \text{H}_2\text{O}$, ...	508, 814
10.	Erythrite, $\text{Co}_3 [\text{As O}_4]_2 \cdot 8 \text{H}_2\text{O}$, ...	509, 817
11.	Annabergite, $\text{Ni}_3 [\text{As O}_4]_2 \cdot 8 \text{H}_2\text{O}$, ...	509, 818
12.	Brushite, $\text{H Ca PO}_4 \cdot 2 \text{H}_2\text{O}$, ...	510, 828

Borates.

1.	Colemanite , $\text{Ca}_2 \text{B}_6 \text{O}_{11} \cdot 5 \text{H}_2\text{O}$, ...	519, 882
2.	BORAX , $\text{Na}_2 \text{B}_4 \text{O}_7 \cdot 10 \text{H}_2\text{O}$, ...	520, 886

Sulphates, Chromates.

1.	Glauberite , $\text{Na}_2 \text{Ca} [\text{SO}_4]_2$, ...	523, 898
2.	Crocoite , Pb Cr O_4 , ...	529, 913
3.	Kainite , $\text{Mg S O}_4 \cdot \text{K Cl} \cdot 3 \text{H}_2\text{O}$, ...	530, 918
4.	Linarite, $[\text{Pb. OH}]_2 \text{SO}_4$, with Cu iso. w. Pb , ...	530, 927
5.	Mirabilite, $\text{Na}_2 \text{SO}_4 \cdot 10 \text{H}_2\text{O}$, ...	531, 931
6.	GYP SUM , $\text{Ca SO}_4 \cdot 2 \text{H}_2\text{O}$, ...	531, 933
7.	Melanterite, $\text{Fe SO}_4 \cdot 7 \text{H}_2\text{O}$, ...	534, 941
8.	Syngenite, $\text{K}_2 \text{Mg} [\text{SO}_4]_2 \cdot \text{H}_2\text{O}$, ...	534, 945
9.	Schoenite , $\text{K}_2 \text{Mg} [\text{SO}_4]_2 \cdot 6 \text{H}_2\text{O}$, ...	535, 948
10.	Polyhalite, $\text{K}_2 \text{Mg Ca}_2 [\text{SO}_4]_4 \cdot 2 \text{H}_2\text{O}$, ...	535, 950
11.	Blödite, $\text{Na}_2 \text{Mg} [\text{SO}_4]_2 \cdot 4 \text{H}_2\text{O}$, ...	535, 946

Tellurites, Selenites.

1.	Emmonsite, hydrated ferric tellurite, ...	538, 979
2.	Chalcomenite, $\text{Cu Se O}_3 \cdot 2 \text{H}_2\text{O}$, ...	538, 980

Tungstates.

1.	WOLFRAMITE , Fe W O_4 , with Mn iso. w. Fe , ...	539, 982
2.	Hübnerite , Mn W O_4 , ...	539, 983

Oxalates.

1.	Whewellite, $\text{Ca C}_2\text{O}_4 \cdot \text{H}_2\text{O}$, ...	993, 542
----	--	----------

TRICLINIC SYSTEM.

Hydroxides.

1. Sassolite, Boracic acid, $B [OH]_3$, ... 352, 255

Carbonates.

1. Lansfordite, $3 Mg CO_3 \cdot Mg [OH]_2 \cdot 2 H_2O$, . . . 367, 305

Silicates.

- | | | | |
|----|---|---|----------|
| 1. | MICROCLINE , $K Al Si_3 O_8$, | | 373, 322 |
| 2. | ALBITE , $Na Al Si_3 O_8$, (Ab), | | 377, 327 |
| 3. | ANORTHITE , $Ca Al_2 Si_2 O_8$, (An), | | 380, 337 |
| | <i>Plagioclase</i> | OLIGOCLEASE-ALBITE , 8 Ab: 1 An, —, —
OLIGOCLEASE , 3 Ab: 1 An, 378, 332
ANDESITE , 1 Ab: 1 An, 379, 333
LABRADORITE , 1 Ab: 3 An, 379, 334
BOYTONITE , 1 Ab: 8 An, —, — | |
| | <i>Feldspars;</i> | | |
| 4. | <i>Albite-</i> | | |
| | <i>Anorthite</i> | | |
| | <i>Series:</i> | | |

5. **RHODONITE**, $Mn Si O_3$, Ca and F iso. w. Mn, . 395, 378
 6. Babingtonite, $(Ca, Fe, Mn) Si O_3$, with $Fe_2 [Si O_3]_3$, 396, 381
 7. **CYANITE**, $Al_2 Si O_6$, ... 434, 500
 8. **Axinite**, $Ca_7 Al_4 B_2 [Si O_4]_8$, Mn, Fe and H_2 iso. w. Ca, 441, 527
 9. Inesite, $2 (Mn, Ca) Si O_3 \cdot H_2O$, ... 452, 564

Phosphates, Arsenates.

1. **Amblygonite**, $Li [Al F] PO_4$, OH iso. w. F, . 503, 781
 2. Roselite, $(Ca, Co, Mg)_3 [As O_4]_2 \cdot 2 H_2O$, . . . 507, 810
 3. Brandtite, $Ca_2 Mn [As O_4]_2 \cdot 2 H_2O$, . . . 507, 811
 4. Fairfieldite, $Ca_2 Mn [PO_4]_2 \cdot 2 H_2O$, . . . 507, 812

Sulphates.

1. **Chalcanthite**, $Cu SO_4 \cdot 5 H_2O$, ... 534, 944
 2. Amarantite, $(Fe, OH) SO_4 \cdot 3 H_2O$, ... 536, 967

MINERALS WHICH ARE AMORPHOUS, MASSIVE,
OR OF UNCERTAIN CRYSTALLIZATION.

Arsenides.

1.	Domeykite, $\text{Cu}_3 \text{As}$, ...	286, 44
2.	Algodonite, $\text{Cu}_6 \text{As}$, ...	286, 45
3.	Whitneyite, $\text{Cu}_9 \text{As}$, ...	286, 45

Oxides, Hydroxides.

1.	Opal , Si O_2 , generally with 3 to 9 % H_2O , ...	329, 194
2.	Turgite , $\text{Fe}_4 \text{O}_6 [\text{OH}]_2$, ...	350, 245
3.	LIMONITE , $\text{Fe}_4 \text{O}_3 [\text{OH}]_6$, ...	350, 250
4.	Xanthosiderite, $\text{Fe}_2 \text{O} [\text{OH}]_4$, ...	350, 251
5.	BAUXITE , $\text{Al}_2 \text{O} [\text{OH}]_4$, ...	350, 251
6.	Psilomelane , Mn O_2 with Mn O , Ba O , Co O , H_2O ?	352, 257

Carbonates.

1.	Bismutosphaerite, $[\text{Bi O}]_2 \text{CO}_3$, ...	364, 290
2.	Hydrozincite, $\text{Zn CO}_3 \cdot 2 \text{Zn} [\text{OH}]_2$?	366, 299
3.	Zaratite, $\text{Ni CO}_3 \cdot 2 \text{Ni} [\text{OH}]_2 \cdot 4 \text{H}_2\text{O}$, ...	367, 306

Silicates.

1.	Deweylite, $\text{Mg}_4 \text{Si}_3 \text{O}_{10} \cdot 6 \text{H}_2\text{O}$?	479, 676
2.	Genthite , $\text{Ni}_2 \text{Mg}_2 \text{Si}_3 \text{O}_{10} \cdot 6 \text{H}_2\text{O}$?	479, 676
3.	Garnierite, Noumeaite , $\text{H}_2 \text{Ni Si O}_4$?	479, 676
4.	Allophane, $\text{Al}_2 \text{Si O}_5 \cdot 5 \text{H}_2\text{O}$, ...	483, 693
5.	CHRYSOCOLLA , $\text{Cu Si O}_3 \cdot 2 \text{H}_2\text{O}$?	483, 699

Phosphates.

1.	Turquoise , $\text{H} [\text{Al} \cdot 2 \text{OH}]_2 \text{PO}_4$, with isomorphous $\text{H} [\text{Cu} \cdot \text{OH}]_2 \text{PO}_4$, ...	512, 844
----	--	----------

PART II.

ARRANGEMENT OF THE MINERALS ACCORDING TO THE ELEMENTS, WITH USES AND STATISTICS.

NOTE.—The chief object of tables of this kind is to call attention to the various chemical combinations of the elements, especially the metals, met with in the mineral kingdom. In each list of minerals the order of the chemical classification of Dana, given on page 2, is followed, and the names are printed in three kinds of type in order to indicate the relative importance of the various compounds, as explained on page 1. For the sake of convenience, the tables follow in alphabetical order, based upon the elements. Following them will be some lists of useful minerals which do not naturally fall under any specific element. Although the lists of minerals are not to be regarded as complete, the attempt has been made to give all of the principal and commercially important combinations. In the case of minerals which are commercially important, their uses are noted and some statistics are given indicating the amount and value of the production. The statistics have been derived chiefly from "*The Mineral Industry for 1901*," published by the Engineering and Mining Journal of New York, and from the "*Mineral Resources of the United States for 1901*," published by the United States Geological Survey.

ALUMINIUM.

Occurrence.—The number of aluminium minerals is so large that no attempt is made to give other than the more important compounds.

CRYOLITE, $\text{Na}_3 \text{Al F}_6$.

CORUNDUM, $\text{Al}_2 \text{O}_3$.

Gibbsite, $\text{Al} [\text{OH}]_3$.

BAUXITE, $\text{Al}_2 \text{O} [\text{OH}]_4$.

FELDSPARS, $\text{K Al Si}_3 \text{O}_8$,

$\text{Na Al Si}_3 \text{O}_8$, $\text{Ca Al}_2 \text{Si}_2 \text{O}_8$, etc.

LEUCITE, $\text{K Al} [\text{Si O}_3]_2$.

NEPHELINE, Na Al Si O_4 .

TOPAZ, $[\text{Al F}]_2 \text{Si O}_4$.

CYANITE, $\text{Al}_2 \text{Si O}_5$.

MICAS, $\text{H}_2 \text{K Al}_3 [\text{Si O}_4]_3$, etc.

KAOLIN, $\text{H}_4 \text{Al}_2 \text{Si}_2 \text{O}_9$.

Pyrophyllite, $\text{H}_2 \text{Al}_2 [\text{Si O}_3]_4$.

THE ZEOLITES.

Lazulite, $\text{Mg} [\text{Al} \cdot \text{OH}]_2 [\text{PO}_4]_2$.

Wavellite, $[\text{Al} \cdot \text{OH}]_3 [\text{PO}_4]_2 \cdot 5 \text{H}_2\text{O}$.

Turquoise, Approx. $\text{H} [\text{Al} \cdot 2 \text{OH}]_2 \text{PO}_4$.

Kalinite, Alum, $\text{K Al} [\text{SO}_4]_2 \cdot 12 \text{H}_2\text{O}$.

Alunite, $\text{K}_2 [\text{Al} \cdot 2 \text{OH}]_6 [\text{SO}_4]_4$.

Uses.—Metallic aluminium and many of its alloys possess highly useful properties. Alum and aluminium sulphate are used in chemical industries, as mordants in dyeing, and extensively in the manufacture of baking powders. The uses of a number of aluminium minerals (corundum, feldspar, mica, kaolin and clay) are explained later under *useful minerals*.

Statistics.—Metallic aluminium is made mostly from bauxite. The domestic production in 1901 was 7,150,000 pounds, valued at \$2,200,000. Price per pound, 31 c. to 37 c.

Alum and aluminium sulphate are made from bauxite, cryolite and alunite. The yearly production of alum is from 7,000 to 20,000 tons, valued at about \$1.75 per 100 pounds, and of aluminium sulphate from 50,000 to 80,000 tons, valued at about \$1.50 per 100 pounds.

The production of bauxite in 1901, mostly from Georgia, Alabama and Arkansas, was 19,000 tons, valued at from \$3.50 to \$4.00 per ton, and the importation was 18,000 tons, valued at \$66,000.

The yearly importation of cryolite, from Greenland, is from 5,000 to 10,000 tons, valued at \$80 per ton.

ANTIMONY.

Occurrence.

Native Antimony, Sb.

STIBNITE, $\text{Sb}_2 \text{S}_3$.

Kermesite, $\text{Sb}_2 \text{S}_2 \text{O}$.

Sulphantimonites,

Pyrargyrite, $\text{Ag}_3 \text{Sb S}_3$.

TETRAHEDRITE, $\text{Cu}_8 \text{Sb}_2 \text{S}_7$, etc.

Senarmontite, $\text{Sb}_2 \text{O}_3$.

Valentinite, $\text{Sb}_2 \text{O}_3$.

Stibiconite, $\text{H}_2 \text{Sb}_2 \text{O}_5$.

Cervantite, $\text{Sb}_2 \text{O}_4$.

Uses.—Metallic antimony is used for making various alloys, type metal, pewter and anti-friction metal. The sulphide is employed in making fire works, percussion caps, matches, and in vulcanizing rubber. Tartar-emetic and antimony sulphide are used for medicinal purposes.

Statistics.—The yearly domestic production of antimony, from stibnite, found mostly in California, Idaho and South Dakota, is from 50 to 250 tons, and from hard lead (antimonial lead from smelting of silver ores) from 1,500 to 2,500 tons. The importation is about 2,500 tons. The value of the domestic and imported product at 10 c. per pound is about \$900,000.

ARSENIC.

*Occurrence.***Native Arsenic**, As.**Niccolite**, Ni As.**Smaltite**, Co As₂.**Chloanthite**, Ni As₂.**Cersdorffite**, Ni As S.Löllingite, Fe As₂.**ARSENOPYRITE**, Fe S As.*Sulpharsenites,***Proustite**, Ag₃ As S₃, etc.**Enargite**, Cu₃ As S₄.*Arsenates,***Mimetite**, Pb₄ [Pb Cl] [As O₄]₃.**Olivenite**, Cu [Cu . OH] As O₄.**Scorodite**, Fe As O₄ . 2 H₂O.

Uses.—Sulphides of arsenic are used as pigment and for pyrotechnics. The oxide is used in medicine, and for poisoning and preserving. Paris green, an arsenate and acetate of copper, is extensively used as pigment and for poisoning.

Statistics.—In 1901 the production of As₂ O₃ at Seattle, Washington, was 600,000 pounds, while the yearly importation, mostly from England and Germany, is about 7,000,000 pounds. The price of As₂ O₃ is from 3½c. to 4½c. per pound.

BARIUM.

*Occurrence.***WITHERITE**, Ba CO₃.Barytocalcite, Ba Ca [CO₃]₂.Hyalophane, 2 K Al Si₃ O₈ . Ba Al₂ Si₂ O₈.Harmotome, (K₂, Ba) Al₂ Si₅ O₁₄ . 5 H₂O.**BARITE**, Ba SO₄.

Uses.—Barite is used chiefly for the production of barium hydroxide, employed in the refining of sugar. Ground barites and precipitated Ba SO₄ are employed as white pigment, for adulterations, and for giving weight and finish to certain grades of paper.

Statistics.—Barite (or barytes) produced in 1901 amounted to nearly 50,000 tons, valued at \$150,000. The supply was obtained from Missouri, Virginia, Tennessee, North Carolina and Georgia. The importation was 5,500 tons, valued at \$40,000.

BERYLLIUM.

*Occurrence.***Chrysoberyl**, Be Al₂ O₄.**BERYL**, Be₃ Al₂ [Si O₃]₆ . ½ H₂O?Leucophanite, Na [Be F] Ca [Si O₃]₂.Helvite, (Mn, Fe)₂ [Mn₂ S] Be₃ [Si O₄]₃.**Phenacite**, Be₂ Si O₄.Euclase, Be [Al . OH] Si O₄.Gadolinite, Be₂ Fe Y₂ Si₂ O₁₀.Bertrandite, H₂ Be₄ Si₂ O₉.Beryllonite, Na Be PO₄.Herderite Ca [Be(OH, F)] PO₄.

Uses.—Some of the beryllium minerals used as gems are noted under a special heading, *gem minerals*. At the present time there is no demand commercially for beryllium or its salts.

BISMUTH.

*Occurrence.***Native Bismuth**, Bi.**Bismuthinite**, $\text{Bi}_2 \text{S}_3$.Tetradymite, $\text{Bi}_2 \text{Te}_2 \text{S}$.*Sulpho-bismuthinites*,Emplectite, $\text{Cu}_2 \text{S} \cdot \text{Bi}_2 \text{S}_3$, etc.Bismutesphaerite $[\text{Bi O}]_2 \text{CO}_3$.Bismutite $[\text{Bi O}] [\text{Bi} \cdot 2 \text{OH}] \text{CO}_3$.Eulytite, $\text{Bi}_4 [\text{Si O}_4]_3$.Pucherite, Bi V O_4 .

Uses.—Bismuth is used for making numerous alloys of low fusing point (solders, safety plugs for boilers and fire extinguishers, and Wood's metal, fusing as low as 60.5°C). Its salts are employed in medicine.

Statistics.—The domestic production of bismuth in 1901, mostly from Colorado, amounted to 600,000 pounds and the importation to 160,000 pounds. The price of refined bismuth ranged from \$1.50 to \$2.25 per pound.

BORON.

*Occurrence.*Sassolite, $\text{B} [\text{OH}]_3$.**Danburite**, $\text{Ca B}_2 [\text{Si O}_4]_2$.**DATOLITE**, $\text{Ca} [\text{B} \cdot \text{OH}] \text{Si O}_4$.**Axinite**, $\text{R}''_7 \text{Al}_4 \text{B}_2 [\text{Si O}_4]_8$.***TOURMALINE**, $\text{R}'_9 \text{Al}_3 [\text{B} \cdot \text{OH}]_2$ $\text{Si}_4 \text{O}_{19}$.§*Borates.***Boracite**, $\text{Mg}_7 \text{Cl}_2 \text{B}_{16} \text{O}_{30}$.**Colemanite**, $\text{Ca}_2 \text{B}_6 \text{O}_{11} \cdot 5 \text{H}_2\text{O}$.**BORAX**, $\text{Na}_2 \text{B}_4 \text{O}_7 \cdot 10 \text{H}_2\text{O}$.**Ulexite**, $\text{Na Ca B}_5 \text{O}_9 \cdot 8 \text{H}_2\text{O}$.* $\text{R}'' = \text{Ca}$ chiefly, with some Fe, Mn and H_2 .§ R' replaced by various elements, Al, Fe, Mg, Mn, Ca, K, Li, Na, H.

Uses.—Borax is used for washing and cleansing; as a solvent of metallic oxides in soldering and welding; and as a flux in numerous smelting and laboratory operations. Borax and boracic acid are also extensively used in pharmaceutical preparations and for their antiseptic properties.

Statistics.—Borax and boracic acid are obtained from the colemanite and native borax deposits of California, Oregon and Nevada. The total value of the products in 1901 amounted to over \$1,000,000.

BROMINE.

*Occurrence.***Embolite**, Ag (Br, Cl).

Bromyrite, Ag Br.

The element is contained also in small quantity in salt brines from which the supply of bromine is obtained.

Uses.—Liquid bromine is employed in numerous chemical industries and in laboratories, and potassium bromide is used extensively in medicine.

Statistics.—The production of bromine in 1901, mostly from Michigan, Ohio, Pennsylvania and West Virginia, was 550,000 pounds, valued at over \$150,000.

CADMIUM.

Occurrence.—Greenockite, Cd S.

The cadmium of commerce is obtained from zinc ores which frequently contain a small quantity of this rare element.

Uses.—The metal is used in making alloys for dental and other purposes. The sulphide is used as a yellow pigment.

Statistics.—Nearly 30,000 pounds of cadmium are produced in Germany, valued at about \$30,000. There is no domestic production.

CAESIUM.

Occurrence.—Pollucite, $H_2 Cs_4 Al_4 [SiO_3]_9$.

This exceptionally rare element is also found in small quantities in beryl and lepidolite, and in the waters of some mineral springs.

CALCIUM.

Occurrence.—Calcium occurs in such a variety of combinations that no attempt is made to give a complete list of its compounds. The typical and more important calcium minerals are as follows :

FLUORITE, $Ca F_2$.**CALCITE**, limestone, and marble,
 $Ca CO_3$.**DOLOMITE**, $Ca Mg [CO_3]_2$.**ARACONITE**, $Ca CO_3$.**Gay-Lussite**, $Na_2 Ca [CO_3]_2 \cdot 5 H_2O$.**ANORTHITE**, $Ca Al_2 [Si O_4]_2$.**WOLLASTONITE**, $Ca Si O_3$.**TITANITE**, $Ca Ti Si O_5$.Perovskite, $Ca Ti O_3$.**APATITE**, $Ca_4 [Ca F] [PO_4]_3$.**Colemanite**, $Ca_2 B_6 O_{11} \cdot 5 H_2O$.**Glauberite**, $Na_2 Ca [SO_4]_2$.**ANHYDRITE**, $Ca SO_4$.**GYPSUM**, $Ca SO_4 \cdot H_2O$.**Scheelite**, $Ca W O_4$.

In addition to the foregoing, calcium is an essential constituent of the following common and important silicates: The lime-soda feldspars, pyroxene, amphibole, grossular and andradite garnets, scapolite, vesuvianite, datolite, epidote, axinite, prehnite and most zeolites.

Uses.—Lime, Ca O , is made by igniting marble and limestone, and is used in mortars and cements, and in a large number of chemical and domestic industries. Marble and limestone rock are extensively quarried for building material and ornamental purposes. Calcium oxide combines with silica and other impurities of ores to form fusible silicates, hence the extensive use of limestone as a *flux* in blast-furnace and other smelting operations. Chalk is Ca CO_3 , and ground chalk, known as *whiting*, is used in putty, for scouring and polishing and for adulterating. Numerous uses are found for precipitated calcium carbonate and for marble dust. Carbon dioxide gas, extensively employed in making effervescent drinks, is largely derived from calcite or marble.

Plaster of Paris is made from gypsum, by heating it at a moderate temperature until about half of its water of crystallization is driven off. Plaster of Paris is extensively used as hard finish in plastering, in making "staff" for the construction of exhibition buildings, and for moulds and casts. Ground gypsum is used to some extent as *land plaster* for fertilizing. Some fibrous and granular varieties of gypsum (satin spar and alabaster) are polished or carved as ornaments.

Statistics.—The yearly consumption of lime is very great, the domestic product being valued at over \$35,000,000. Lime is worth about \$1 per barrel of 250 lbs. The domestic production of limestone in 1901 was valued as follows: Building and structural stone, \$6,000,000; broken stone for railroad ballast, macadam, concrete and rubble, \$6,000,000; for making lime, \$8,000,000; for blast-furnace flux, \$4,500,000; and for use in Portland cement, \$500,000; a total of \$25,000,000.

The production of gypsum in 1901 amounted to 650,000 tons, valued at \$1,500,000, the supply coming chiefly from Michigan, New York, Iowa, Kansas, Oklahoma, Texas and Virginia. The importation of gypsum and plaster of Paris is valued at \$300,000. Ground gypsum for land plaster is worth about \$2 per ton, plaster of Paris about \$3.50 per ton.

CARBON.

*Occurrence.***DIAMOND, C.****GRAPHITE, C.**

Carbon is the characteristic non-metallic constituent of all *carbonates*, see pages 353 to 267 of Dana's Text Book of Mineralogy. Although not regarded as minerals in the strict sense of being definite chemical compounds, the various forms of coal, petroleum, natural gas, asphaltum and mineral wax (ozokerite) are exceedingly important substances, generally classed as mineral products.

Uses.—Diamonds are used as gems and for cutting and polishing hard materials. Graphite is used for pencils, for making refractory crucibles, as a lubricant, and as stove polish and pigment for brightening and protecting iron surfaces. Heavy mineral oils are used as lubricants; solid products, such as paraffin and ozokerite, for candles, wax papers, and as protecting and insulating substances. Asphaltum is extensively employed in making pavements and asphaltum varnishes.

Statistics.—The value of the diamonds imported into the United States in 1901 was about \$21,000,000, including over \$800,000 worth of diamond dust.

The graphite produced in 1901 was 4,000,000 pounds, valued at \$135,000, mostly derived from Ticonderoga, N. Y.; Chester Co., Pa., and Barton Co., Ga. The value of imported graphite was \$900,000. At Niagara Falls 2,500,000 pounds of artificial graphite were produced by electricity.

For coal and fuel the figures for 1901 are as follows: Anthracite from Pennsylvania, 67,000,000 tons, \$112,000,000; bituminous coal, mostly from Pennsylvania, Illinois, Ohio, West Virginia and Alabama, 225,000,000 tons, \$235,000,000; crude petroleum, mostly from Pennsylvania, Ohio, California, Indiana and Texas, 69,000,000 barrels of 42 gallons, \$80,000,000. The value of illuminating oil exported was \$50,000,000; of other grades, \$20,000,000. Natural gas, mostly from Pennsylvania, Ohio and Indiana, equivalent to 8,500,000 tons of coal, \$27,500,000.

Asphaltum obtained in 1891, mostly from California, Utah and Texas, was valued at over \$350,000; while bituminous sandstone from California and Kentucky, and asphaltic limestone from Indian Territory and Texas were valued at over \$150,000. Over 110,000 tons of asphaltum were imported into the United States from Trinidad.

Large quantities of mineral wax, ozokerite, are imported from Austria, where it occurs in extensive deposits.

CERIUM.

Together with cerium the so-called *Rare Earth Metals*, lanthanum, didymium, yttrium, erbium and thorium, will be considered. In the chemical formulas it is understood that Ce expresses the elements of the cerium group, Ce, La and Di; and Y the elements of the yttrium group, Y and Er.

Occurrence.

Tysonite, Ce F_3 .

Parosite, $\text{Ca} [\text{Ce F}]_2 [\text{C O}_3]_3$.

Bastnäsite, $[\text{Ce F}] \text{C O}_3$.

Lanthanite, $\text{La}_2 [\text{CO}_3]_3 \cdot 9 \text{H}_2\text{O}$.

Thorite, Th Si O_4 .

Allanite, $\text{Ca}_2 [\text{R. OH}] \text{R}_2 [\text{SiO}_4]_3$.

R = Al, Fe, Ce and Y.

Gadolinite $\text{Be}_2 \text{Fe Y}_2 \text{Si}_2 \text{O}_{10}$.

Cerite, $\text{H}_6 \text{Ce}_4 \text{Si}_3 \text{O}_{15}?$

Most niobates and tantalates.

Xenotime, Y PO_4 .

Monazite, Ce PO_4 , with Th Si O₄.

Uses.—Thorium, an exceedingly rare element, is used for making incandescent mantles for Welsbach and other lights. The incandescent material is *thoria*, Th O_2 mixed with a little oxide of cerium, and is mostly obtained from monazite.

Statistics.—The production of monazite in 1901, mostly from North Carolina, was 750,900 pounds, valued at \$60,000.

CHLORINE.

Chlorine is the characteristic non-metallic constituent of the chlorides, see Dana's Text Book of Mineralogy, pages 317 to 323. Halite or rock salt, Na Cl , is the most important mineral containing it.

Uses.—Hydrochloric or muriatic acid and bleaching powder, chloride of lime, are extensively used in chemical, metallurgical and manufacturing industries, and their production is generally connected with that of caustic soda. Large quantities of bleaching powder are used in the chlorination process of extracting gold from ores.

CHROMIUM.

Occurrence.

CHROMITE, Fe Cr O_4 with Mg Cr O_4 . **Crocoite**, Pb Cr O_4 .

Uvarovite, $\text{Ca}_3 (\text{Al, Cr})_2 [\text{Si O}_4]_3$.

Uses.—The oxides $\text{Cr}_2 \text{O}_3$ (green) and Cr O_3 (red), potassium dichromate, lead chromate, and chrome alum are used as pigments and for dyeing and calico printing. Another demand for chrome ore is for making *chrome-steel*, which possesses superior hardness and toughness, and is used in making projectiles, armor plate and safes. For this purpose an alloy of iron and chromium (ferro-

chromium) is made in electric furnaces and this is added to molten steel. Considerable chromite is also employed in making *chrome bricks*, which are very refractory and are used for lining furnaces.

Statistics.—The production of chrome ore in 1901, from California, was 500 tons, valued at \$7,500. The importation was 20,000 tons, valued at \$350,000.

COBALT.

Occurrence.

Linnæite, $\text{Co}_3 \text{S}_4$.

Smaltite, Co As_2 .

Cobaltite, Co S As .

Glaucodot, $(\text{Co}, \text{Fe}) \text{S As}$.

Erythrite, $\text{Co}_3 [\text{As O}_4]_2 \cdot 8 \text{H}_2\text{O}$.

Some cobalt is found in most nickel minerals, and the most abundant supply of this rare metal is derived from cobaltiferous manganese oxide found in New Caledonia.

Uses.—Cobalt oxide is the chief product demanded by the trade and is used for giving blue colors to glass and porcelain. Smalt is a blue pigment made by grinding glass and other silicates colored by cobalt oxide.

Statistics.—The domestic production of cobalt oxide in 1901 was 13,000 pounds, derived as bi-product in the treatment of lead ores at Mine La Motte, Mo. The importation was 70,000 pounds. Cobalt oxide is worth about \$2.25 per pound.

COLUMBIUM,—SEE NIOBIUM.

COPPER.

NATIVE COPPER, Cu .

Domeykite, $\text{Cu}_3 \text{As}$.

Algodonite, $\text{Cu}_6 \text{As}$.

Whitneyite, $\text{Cu}_9 \text{As}$.

Berzelianite, $\text{Cu}_2 \text{Se}$.

Rickardite, $\text{Cu}_4 \text{Te}_3$.

CHALCOCITE, $\text{Cu}_2 \text{S}$.

Stromeyerite, Cu Ag S .

Covellite, Cu S .

BORNITE, $\text{Cu}_3 \text{Fe S}_3$.

CHALCOPYRITE, Cu Fe S_2 .

Chalcostibite, Cu Sb S_2 .

Emplectite, Cu Bi S_2 .

TETRAHEDRITE, $\text{Cu}_8 \text{Sb}_2 \text{S}_7$.

Tennantite, $\text{Cu}_8 \text{As}_2 \text{S}_7$.

Enargite, $\text{Cu}_3 \text{As S}_4$.

Atacamite, $\text{Cu}_2 \text{Cl} [\text{OH}]_3$.

CUPRITE, $\text{Cu}_2 \text{O}$.

Tenorite (Melaconite), Cu O .

MALACHITE, $[\text{Cu} \cdot \text{OH}]_2 \text{CO}_3$.

AZURITE, $[\text{Cu} \cdot \text{OH}]_2 \text{Cu} [\text{CO}_3]_2$.

Dioptase, $\text{H}_2 \text{Cu Si O}_4$.

CHRYSOCOLLA, $\text{Cu Si O}_3 \cdot 2 \text{H}_2\text{O}?$

Olivenite, $\text{Cu} [\text{Cu} \cdot \text{OH}] \text{As O}_4$.

Libethenite, $\text{Cu} [\text{Cu} \cdot \text{OH}] \text{PO}_4$.

Clinoclasite, $[\text{Cu} \cdot \text{OH}]_3 \text{As O}_4$.

Euchroite, $\text{Cu} [\text{Cu} \cdot \text{OH}] \text{As O}_4 \cdot 3 \text{H}_2\text{O}$.

Chalcophyllite, $\text{Cu}_4 [\text{OH}]_5 \text{As O}_4$.

$3\frac{1}{2} \text{H}_2\text{O}$.

Gerhardtite, $\text{Cu}_4 [\text{OH}]_6 [\text{NO}_3]_2$.

Spangolite, $\text{Cu}_6 \text{Al Cl SO}_{10} \cdot 9 \text{H}_2\text{O}$.

Brochantite, $\text{Cu}_4 [\text{OH}]_6 \text{SO}_4$.

Chalcanthite, $\text{Cu SO}_4 \cdot 5 \text{H}_2\text{O}$.

Chalcomenite, $\text{Cu Se O}_3 \cdot 2 \text{H}_2\text{O}$.

Uses.—Copper wire, sheet and nails are used extensively, wire especially for conductors of electricity and in electrical apparatus. One of the chief uses of copper is in making alloys: notably brass,

copper and zinc; bronze, copper and tin, frequently also zinc; German silver or white metal, copper, zinc and nickel. Some alloys with aluminium are useful because of their color and high tensile strength. Copper sulphate or blue vitriol is employed in calico printing, in the manufacture of various copper salts, in galvanic cells, and in numerous manufacturing industries.

Statistics.—The domestic production of copper in 1901 was about 600,000,000 pounds, valued (at 12c. per pound) at \$72,000,000, and mostly derived from the following states in the order named: Montana, Michigan (155,000,000 pounds from native copper), Arizona, California, Utah and Colorado. Just about one-half of the world's production of copper is from the United States. The price of copper in 1901 ranged from 14c. to 16½c. per pound, while the average price for 1902 was about 12c. The production of copper sulphate, blue vitriol, in 1901 was 78,000,000 pounds, worth about 4½c. per pound.

DIDYMIUM }
 ERBIUM } See Cerium, page 30.

FLUORINE.

Occurrence.—Fluorine is the characteristic non-metallic constituent of the fluorides, see Dana's Text Book of Mineralogy, pages 317 to 323. Fluorite, Ca F_2 , and cryolite, $\text{Na}_3 \text{Al F}_6$, are the only commercially important fluorides. Fluorine occurs as a constituent of several carbonates, silicates and phosphates, frequently with hydroxyl or chlorine isomorphous with it: Some notable examples are as follows:

Parisite, $\text{Ca} [\text{Ce F}]_2 [\text{CO}_3]_3$.

Bastnäsite, $[\text{Ce F}] \text{CO}_3$.

Zunyte, $[\text{Al}_2(\text{OH}, \text{F}, \text{Cl})]_6 \text{Al}_2 [\text{Si O}_4]_3$.

TOPAZ, $[\text{Al F}]_2 \text{Si O}_4$, often with $[\text{Al} \cdot \text{OH}]_2 \text{Si O}_4$.

LEPIDOLITE, $\text{K Li} [\text{Al} \cdot 2 (\text{OH}, \text{F})] \text{Al} [\text{Si O}_3]_3$.

Herderite, $\text{Ca} [\text{Be} (\text{OH}, \text{F})] \text{PO}_4$.

APATITE, $\text{Ca}_4 [\text{Ca F}] [\text{PO}_4]_3$ and

$\text{Ca}_4 [\text{Ca} (\text{F}, \text{Cl})] [\text{PO}_4]_3$.

Wagnerite, $[\text{Mg F}] \text{Mg PO}_4$.

Triplite, $[\text{R F}] \text{R PO}_4$; $\text{R} = \text{Fe}$ and Mn .

Durangite, $\text{Na} [\text{Al F}] \text{As O}_4$.

Amblygonite, $\text{Li} [\text{Al F}] \text{PO}_4$ and $\text{Li} [\text{Al} (\text{OH}, \text{F})] \text{PO}_4$.

Uses.—Fluorite is used chiefly as a flux in furnaces in which steel and iron are melted; also in the manufacture of opalescent glass and for making hydrofluoric acid, H F , for etching glass. The uses of cryolite are noted on page 24.

Statistics. The production of fluorite in 1901 was 19,500 tons, valued at \$113,000, the mineral coming from Eastern Kentucky and Southern Illinois. Fluorite is worth about \$14 per ton, \$17 to \$18 when ground.

GALLIUM.

Occurrence.—Traces of this very rare element have been found in sphalerite from a few localities.

GERMANIUM.

Occurrence.

Argyrodite, $\text{Ag}_8 \text{Ge S}_6$.

Canfieldite, $\text{Ag}_8 (\text{Sn, Ge}) \text{S}_6$.

GOLD.

Occurrence.

NATIVE GOLD, Au, but always containing some silver.
 Petzite, $[\text{Ag, Au}]_2 \text{Te}$.

Sylvanite, Au Ag Te_4 .
 Krennerite, Au Te_2 .
Calaverite, Au Te_2 .

Gold is found in many pyritiferous and other sulphide ores, and often it is impossible to tell in just what combination it occurs: This is because of the small amount of gold in most ores; thus a ton of ore having one per cent. of gold would contain 291.66 troy ounces of the precious metal, worth \$6,028, hence what may be called a rich ore, with gold value of \$60 per ton, would contain but 0.01 per cent. of gold. The occurrence of gold in combination with tellurium and associated with tellurium minerals is worthy of note.

Uses.—The uses of gold for coin, ornaments and plating are well known. The standard gold for United States coin is 9-10ths fine, 9 parts of gold to 1 of copper. The gold used in jewelry is hardened by alloying it with copper and silver; 18 carat fine being 18-24ths gold and 6-24ths other metals.

Statistics.—The domestic production of gold in 1901 was 3,880,000 fine ounces, valued at \$80,000,000, derived from the following states, the numbers giving the nearest million dollars: Colorado 29, California 16, Alaska 7, South Dakota 6.5, Montana 5, Arizona 4, Utah 4, Nevada 3, Idaho 2.3 and Oregon 1.8. The world's production in 1901 was valued at \$250,000,000. Gold is the standard of value and a troy ounce is worth \$20.67, equivalent to \$301.44 per pound avoirdupois.

HYDROGEN.

Occurrence.—Hydrogen occurs in combination with oxygen in water and ice, and in the water of crystallization and hydroxyl radicals of many minerals. In combination with carbon it occurs in hydrocarbons, bituminous coal, petroleum and natural gas.

INDIUM.

Occurrence.—This excessively rare metal is found in small quantity in sphalerite from a few localities.

IODINE.

Occurrence.

Marshite, Cu I .
Miersite, $4 \text{ Ag I} \cdot \text{Cu I}$.

Iodyrite, Ag I .
Lautarite, $\text{Ca} [\text{IO}_3]_2$.

Uses.—Iodine and its compounds are used in chemical industries and laboratories, and in pharmaceutical preparations.

Statistics.—At the present time most of the iodine of commerce comes from Chile, where the production in 1901 was valued at \$4,000,000. Iodine is worth about \$2.75 per pound.

IRIDIUM.

Occurrence.—This rare metal is found sparingly with platinum ores as platiniridium and iridosmine.

Uses.—On account of stability and superior hardness platinum-iridium alloys have been employed for making standard weights and measures of the highest grade. Hard iridium alloys are used for tipping gold pens.

Statistics.—In 1901 the production of iridium from California ores amounted to 250 ounces, valued at \$5,000.

IRON.

Occurrence.—Only typical iron compounds are included in the accompanying table, and it should be noted that iron occurs as an isomorphous constituent in many minerals, especially silicates and phosphates, replacing magnesium and manganese when *ferrous*, and aluminium when *ferric*.

NATIVE IRON, Fe with Ni .

PYRRHOTITE, $\text{Fe}_{11} \text{S}_{12}$.

PYRITE, Fe S_2 .

MARCASITE, Fe S_2 .

HEMATITE, $\text{Fe}_2 \text{O}_3$.

ILMENITE, Fe Ti O_3 .

MAGNETITE, $\text{Fe}_3 \text{O}_4$.

Turgite, $\text{Fe}_4 \text{O}_5 [\text{OH}]_2$.

CÖTHITE, $\text{Fe}_2 \text{O}_2 [\text{OH}]_2$.

LIMONITE, $\text{Fe}_4 \text{O}_3 [\text{OH}]_6$.

SIDERITE, Fe CO_3 .

ALMANDITE, $\text{Fe}_3 \text{Al}_2 [\text{Si O}_4]_3$.

ANDRADITE, $\text{Ca}_3 \text{Fe}_2 [\text{Si O}_4]_3$.

Fayalite, $\text{Fe}_2 \text{Si O}_4$.

Ilvaite, $\text{Ca Fe}_2 [\text{Fe} \cdot \text{OH}] [\text{Si O}_4]_2$.

COLUMBITE, $(\text{Fe}, \text{Mn})(\text{Nb}, \text{Ta})_2 \text{O}_6$.

Triphylite, Li Fe PO_4 .

Vivianite, $\text{Fe}_3 [\text{PO}_4]_2 \cdot 8 \text{H}_2\text{O}$.

Scorodite, $\text{Fe As O}_4 \cdot 2 \text{H}_2\text{O}$.

Melanterite, $\text{Fe SO}_4 \cdot 7 \text{H}_2\text{O}$.

Jarosite, $\text{K}_2 \text{Fe}_6 [\text{OH}]_{12} [\text{SO}_4]_4$.

WOLFRAMITE, Fe WO_4 .

In connection with the iron industry it should be noted that ores must contain a high percentage of iron, thus an average Lake Superior ore contains in the neighborhood of 60 % Fe. Practically the only minerals which are mined as iron ores are hematite, magnetite and limonite, rarely siderite. It should also be noted that phosphorus, sulphur and titanium are injurious constituents of ores, notably phosphorus, which in a high grade

Bessemer ore should not exceed 0.05 per cent. The importance of limestone as a blast-furnace flux is noted on page 28. The importance of manganese is noted on page 38.

Uses.—The customary uses of iron and steel in the arts need no special comment. The most important commercial salt of iron is copperas, green vitriol, $\text{Fe SO}_4 \cdot 7 \text{H}_2\text{O}$, employed in dyeing, in making rouge, inks and Prussian blue, and as a disinfectant. Rouge, $\text{Fe}_2 \text{O}_3$, made from copperas, is used as polishing powder and pigment, when it is known as Venetian and Indian red. Considerable soft iron ore is ground for mineral paint, ocher, umber, sienna and iron oxide.

Iron oxides may be made to combine with silica to form fusible silicates, hence the uses of iron ores as fluxes in some smelting operations, notably in the smelting of silver ores.

Much attention is now being paid to the combination of small quantities of nickel, chromium, tungsten, titanium and molybdenum with steel in order to obtain metal of superior hardness, toughness and tempering qualities.

Statistics.—The total production of domestic ores in 1901, mostly hematite, was nearly 29,000,000 long tons (2,240 lbs.); 11,000,000 from Minnesota, 9,500,000 from Michigan and Wisconsin, 4,500,000 from Alabama and southern states, and 3,500,000 from other sources. The iron ore imported was about 1,000,000 tons.

The domestic production of pig iron was nearly 16,000,000 long tons, which, at an average price of \$15.50 per ton, amounts to a total value of \$248,000,000.

The production of Bessemer and open hearth steel in 1901 was 13,500,000 tons, worth about \$27.50 per ton when rolled into rails.

The world's production of pig iron in 1901 was 40,000,000 tons, and of steel 31,000,000 tons.

The yearly production of pig iron in the United States has practically doubled with every decade since 1872, as shown by the following, the amount being long tons :

Year,	1872,	1882,	1892,	1901,
Tons,	2,500,000.	4,500,000.	8,300,000.	16,000,000.

The production of copperas, mostly as a bi-product, amounted in 1901 to 23,500 tons, valued at \$112,000. The average price per ton in New York is from \$10 to \$14.

The production of iron ores ground as mineral paint was 43,000 tons, valued at \$500,000. The value of similar imported products amounted to about \$100,000.

Occurrence.

Native lead, Pb.

CALENA, Pb S.

Altaite, Pb Te.

Clausthalite, Pb Se.

Zinkenite, Pb Sb₂ S₄.Sartorite, Pb As₂ S₄.Jamesonite, Pb₂ Sb₂ S₅.Dufrenoyite, Pb₂ As₂ S₅.Cosalite, Pb₂ Bi₂ S₅.Meneghinite, Pb₄ Sb₂ S₇.Cotunite, Pb Cl₂.Percylite, Pb Cu [OH]₂ Cl₂.Matlockite, Pb₂ O Cl₂.

Massicot, Pb O.

Minium, Pb₃ O₄.Plattnerite, Pb O₂.**CERUSSITE**, Pb CO₃.**Phosgenite**, [Pb Cl]₂ CO₃.Leadhillite, Pb₂ [Pb. OH]₂ [CO₃]₂ SO₄.Barysilite, Pb₃ Si₂ O₇.Nasonite, Pb₄ [Pb Cl]₂ Ca₄ [Si₂ O₇]₃.Ganomalite, Pb₄ [Pb. OH]₂ Ca₄ [Si₂ O₇]₃.Melanotekite, [Fe₄ O₃] Pb₃ [Si O₄]₃.Kentrolite, [Mn₄ O₃] Pb₃ [Si O₄]₃.**PYROMORPHITE**, Pb₄ [Pb Cl]
[PO₄]₃.**Mimetite**, Pb₄ [Pb Cl] [As O₄]₃.**Vanadinite**, Pb₄ [Pb Cl] [VO₄]₃.Descloizite, (Pb, Zn)₂ [OH] VO₄.**ANGLESITE**, Pb SO₄.**Crocoite**, Pb Cr O₄.**Wulfenite**, Pb Mo O₄.Stolzite, Pb WO₄.

The almost universal association of minerals containing silver and zinc with lead ores is worthy of special note, in fact a large part of the lead of commerce is so-called *desilverized lead*, obtained from the smelting of silver ores.

Uses.—Lead is extensively used as sheet and pipe by plumbers, as ballast for small vessels, for making weights, bullets, shot and washers, and numerous useful alloys. Ordinary solder is made of lead and tin, type metal of lead and antimony, low-fusion alloys of lead, bismuth and tin. Much so-called tin foil contains considerable lead. Litharge, Pb O, is largely employed in making flint glass and glazing earthenware. Minium, Pb₃ O₄, is a red pigment and is used in glass making. White lead, [Pb. OH]₂ Pb [CO₃]₂, is the basis of the best white paint, having great covering power. Lead chromates are employed as yellow and red pigments. Lead acetate, sugar of lead, is the most important soluble salt, used largely in the arts.

Statistics. The production from domestic ores in 1901 was 280,000 tons of lead valued at \$24,000,000, of which 210,000 tons was desilverized lead. The states producing the largest quantities are Colorado, Idaho, Missouri, Utah and Montana. The average price of lead in New York during 1901 was 4 1/3c. per pound. The production of litharge was 10,000 tons valued at \$1,200,000, of red lead 13,000 tons valued at \$1,500,000, and of white lead 100,000 tons valued at \$11,000,000.

LITHIUM.

*Occurrence.*Petalite, $\text{Li Al Si}_4 \text{O}_{10}$.**SPODUMENE**, $\text{Li Al Si}_2 \text{O}_6$.Eucryptite, Li Al Si O_4 .**LEPIDOLITE**, $\text{Li K [Al}_2 (\text{OH}, \text{F})]$ $\text{Al [Si O}_3\text{]}_3$.**Triphylite**, Li Fe PO_4 .**Lithiophilite**, Li Mn PO_4 .**Amblygonite**, Li [Al F] PO_4 , with $\text{Li [Al (OH}, \text{F})] PO}_4$.

Small quantities of lithia are found in some natural spring waters and in a number of silicates, notably the micas, tourmaline and beryl.

Uses.—Lithia waters and lithia salts have medicinal properties, used especially in the treatment of rheumatism and gout. Pure lithia salts are valuable in the laboratory for making monochromatic red light.

Statistics.—Lepidolite is the chief commercial source of lithia, and 1,750 tons, valued at \$43,000, were mined in San Diego County, California, in 1901, and exported to Germany for treatment. The average price paid was nearly \$25 per ton.

MAGNESIUM.

Occurrence.—Magnesium is an element of very common occurrence, especially as a component of a number of silicates which play an important rôle as rock constituents. The isomorphous replacement of some magnesium by ferrous iron is very common. All of the more important types of magnesium compounds are given in the accompanying table, but the list is not a complete one.

Sellaite, Mg F_2 .Bischofite, $\text{Mg Cl}_2 \cdot 6 \text{H}_2\text{O}$.**Carnallite**, $\text{K Cl} \cdot \text{Mg Cl}_2 \cdot 6 \text{H}_2\text{O}$.Tachydrite, $\text{Ca Cl}_2 \cdot 2 \text{Mg Cl}_2 \cdot 12 \text{H}_2\text{O}$.Periclase, Mg O .**SPINEL**, $\text{Mg Al}_2 \text{O}_4$.**BRUCITE**, Mg [OH]_2 .**DOLOMITE**, $\text{Ca Mg [CO}_3\text{]}_2$.**MAGNESITE**, Mg CO_3 .Nesquehonite, $\text{Mg CO}_3 \cdot 3 \text{H}_2\text{O}$.Hydromagnesite, $\text{Mg}_4 [\text{OH}]_2 [\text{CO}_3]_3 \cdot$ $3 \text{H}_2\text{O}$.Lansfordite, $\text{Mg}_4 [\text{OH}]_2 [\text{CO}_3]_3 \cdot 21 \text{H}_2\text{O}$.**ENSTATITE-BRONZITE**,
(Mg, Fe) Si O_3 .Pyroxene, $\text{Ca [Mg}, \text{Fe}] [\text{Si O}_3]_2$.Anthophyllite (Mg, Fe) Si O_3 .**AMPHIBOLE**, R Si O_3 , $\text{R}=\text{Mg}$, $\text{Fe} \text{ \& \; Ca}$.Monticellite, Ca Mg Si O_4 .**CHRYSolITE**, $[\text{Mg}, \text{Fe}]_2 \text{Si O}_4$.**Chondrodite**, $[\text{Mg (F}, \text{OH})]_2 \text{Mg}_3$ $[\text{Si O}_4]_2$.Humite, $[\text{Mg (F}, \text{OH})]_2 \text{Mg}_3 [\text{Si O}_4]_3$.Clinohumite, $[\text{Mg (F}, \text{OH})]_2 \text{Mg}_7$ $[\text{Si O}_4]_4$.**THE MICAS, BIOTITE AND
PHLOGOPITE.****THE CHLORITES, CLINO-
CHLORE.****SERPENTINE**, $\text{H}_4 \text{Mg}_3 \text{Si}_2 \text{O}_9$.**TALC**, $\text{H}_2 \text{Mg}_3 [\text{Si O}_3]_4$.Wagnerite, $[\text{Mg F}] \text{Mg PO}_4$.**Boracite**, $\text{Mg}_7 \text{Cl}_2 \text{B}_{16} \text{O}_{30}$.**Kainite**, $\text{Mg SO}_4 \cdot \text{K Cl} \cdot 3 \text{H}_2\text{O}$.**Schoenite**, $\text{K}_2 \text{Mg [SO}_4\text{]}_2 \cdot 6 \text{H}_2\text{O}$.Epsomite, $\text{Mg SO}_4 \cdot 7 \text{H}_2\text{O}$.Blödite, $\text{Mg SO}_4 \cdot \text{Na}_2 \text{SO}_4 \cdot 4 \text{H}_2\text{O}$.

Uses.—Magnesite when calcined yields magnesia, Mg O , which when compressed into bricks is used for refractory furnace lining. Magnesia is also used in making non-conductive covering for boilers and steam pipes. Magnesia salts, especially the sulphate, are used in the arts and to some extent in pharmaceutical preparations. Many limestones and marbles approximate to dolomite in composition, when they are called dolomitic, and some of them are valuable building stones. Some varieties of magnesia mica, serpentine and talc are used in the arts, and will be referred to in a later paragraph.

Statistics.—The production of magnesite is limited to California, where 13,000 tons were produced in 1901, valued at \$43,000. The importation of magnesite amounts to about 33,000 tons. The production of epsom salts, $\text{Mg SO}_4 \cdot 7 \text{ H}_2\text{O}$, made as a bi-product, was estimated to have been 8,000,000 pounds in 1900.

MANGANESE.

Alabandite, Mn S .Hauerite, Mn S_2 .Manganosite, Mn O .**Franklinite**, (Fe, Mn, Zn) $(\text{Fe, Mn})_2 \text{O}_4$.Hausmannite, $\text{Mn}_3 \text{O}_4$.Braunite, Mn, (Mn, Si) O_3 .Bixbyite, Fe Mn O_3 .Polianite, Mn O_2 .**MANGANITE**, $\text{Mn}_2 [\text{OH}]_2 \text{O}_2$.**PYROLUSITE**, Mn O_2 with water?Pyrochroite, $\text{Mn} [\text{OH}]_2$.**Psilomelane**, Mn O_2 , Mn O , etc.**RHODOCHROSITE**, Mn C O_3 .**RHODONITE**, Mn Si O_3 .Helvite, $(\text{Mn, Fe})_2 [\text{Mn}_2 \text{S}] \text{Be}_3 [\text{Si O}_4]_3$.**Spessartite**, $\text{Mn}_3 \text{Al}_2 [\text{Si O}_4]_3$.Glaucochroite, Ca Mn Si O_4 .Tephroite, $\text{Mn}_2 \text{Si O}_4$.Friedelite, $\text{H}_7 [\text{Mn Cl}] \text{Mn}_4 [\text{Si O}_4]_4$.Piedmontite, $\text{Ca}_2 [\text{Al . OH}] (\text{Al, Mn})_2 [\text{Si O}_4]_3$.Inesite, $3 (\text{Mn, Ca}) \text{Si O}_3 \cdot 2 \text{H}_2\text{O}$.**Lithiophilite**, Li Mn PO_4 .Triplite, $[\text{R F}] \text{R P O}_4$, $\text{R} = \text{Mn \& Fe}$.Tripliodite, $[\text{R . OH}] \text{R PO}_4$, $\text{R} = \text{Mn and Fe}$.Sussexite, H R B O_3 , $\text{R} = \text{Mn, Mg \& Zn}$.**Hübnerite**, Mn W O_4 .

A number of common minerals, notably silicates, contain from traces to several per cent. of oxide of manganese, which is isomorphous with the oxides of iron and magnesium.

Uses.—Manganese ores are used chiefly in making ferro-manganese and spiegeleisen, compounds which are employed in the manufacture of steel. A little metallic manganese is produced by the electrical furnace and alloyed with copper for making manganese bronze. Some oxide of manganese is employed by glass makers: When added in proper amount to molten glass the violet color which manganese tends to impart destroys (complements) the yellow caused by oxide of iron, and thus a nearly colorless product is obtained. The higher oxides of manganese are used in

laboratories for obtaining oxygen gas and for liberating chlorine from hydrochloric acid. In some regions, notably Colorado, silver ores contain sufficient manganese (generally rhodochrosite) to make it of decided value as a flux.

Statistics.—The production of manganese ores in 1901, from Michigan, Wisconsin, Colorado, New Jersey, Virginia and Georgia, amounted to 600,000 long tons (2,240 lbs.), valued at over \$1,500,000. The importation was 165,000 tons, valued at \$1,500,000. It is very important that manganese ores should be low in phosphorus, less than 0.10 per cent.

MERCURY, QUICKSILVER.

Occurrence.

Native Mercury, Hg.	Onofrite, Hg (S, Se).
Native Amalgam, Hg with Ag.	Coloradoite, Hg Te.
Metacumabarite, Hg S.	CINNABAR , Hg S.
Tiemannite, Hg Se.	Calomel, Hg Cl.

Uses.—Metallic mercury is used extensively in the amalgamation processes of extracting gold and silver from ores, in the manufacture of physical and chemical apparatus, and in a variety of chemical and electrical industries. The silvering on mirrors is an amalgam of tin and mercury. Mercury salts are extensively employed in pharmaceutical preparations, and the sulphide is the red pigment vermilion.

Statistics.—Quicksilver is generally sold in bulk by the flask of 76½ lbs. The production in 1901 was nearly 30,000 flasks, or 1,100 tons, valued at about \$1,400,000, nine-tenths of the supply coming from California, the remainder from Texas. A little less than one-third of the world's production of quicksilver in 1901 was produced in the United States. The price of mercury per flask at San Francisco is about \$50.

MOLYBDENUM.

Occurrence.

MOLYBDENITE , Mo S ₂ .	Wulfenite , Pb Mo O ₄ .
Molybdate, Mo O ₃ .	Powellite, Ca Mo O ₄ .

Uses.—Ammonium molybdate is used in all chemical laboratories for the detection and estimation of phosphoric acid. A recent and large demand for molybdenum is for making ferro-molybdenum: This when combined with chrome-steel gives a product which is self-hardening.

Statistics.—Only a little molybdenite is produced in the United States, the price, however, for nearly pure mineral is about \$400 per ton. The domestic production of molybdenum and ferromolybdenum for the steel industry amounted in 1901 to 35,000 and 16,000 pounds respectively, valued at about \$70,000.

NICKEL.

Meteoric and native nickel-iron, awaruite and josephinite, Fe with Ni.

Pentlandite, (Ni, Fe) S.

Millerite, Ni S.

Niccolite, Ni As.

Breithauptite, Ni Sb.

NICKELIFEROUS PYRRHOTITE.

Linnaeite, (Co, Ni, Fe)₃ S₄.

Melonite, Ni₂ Te₃.

Chloanthite, Ni As₂.

Gersdorffite, Ni As S.

Ullmanite, Ni Sb S.

Rammelsbergite, Ni As₂.

Zaratite, Ni₃ [OH]₄ CO₃ · 4 H₂O.

Genthite, Ni₂ Mg₂ Si₃ O₁₀ · 6 H₂O?

Garnierite, noumeaite, H₂ Ni SiO₄?

Annabergite, Ni₃ [As O₄]₂ · 8 H₂O.

Morenosite, Ni SO₄ · 7 H₂O.

Uses.—The chief demand for nickel is for making *nickel-steel*, which contains about 3½ per cent. of nickel, possesses great strength and toughness, and is used for armor plate. For various uses in the steel industry products known as ferro-nickel, chrom-nickel, tungsten-nickel and molybdenum-nickel are manufactured. There are numerous important alloys of nickel: German silver containing Cu, Zn and Ni; metal for coinage containing Cu and Ni; and also some alloys with aluminium which possess great strength. Considerable metal is used in nickel plating.

Statistics.—Owing to the rare occurrence of nickel minerals the production of nickel from domestic ores amounts to but a few thousand pounds a year, mostly obtained as a bi-product from the treatment of lead ores at Mine La Motte, Mo. The production from foreign ores, chiefly pyrrhotite and pentlandite from Sudbury, Canada, amounted in 1901 to about 8,500,000 pounds, valued at \$4,000,000. Next in importance to the sulphide ores of Sudbury come the silicate (garnierite) deposits of New Caledonia. The world's production of nickel in 1901 amounted to 20,000,000 pounds. An average price for nickel is about 50c. per pound.

NIOBIUM, called also COLUMBIUM.

Occurrence.—Niobium is a rare non-metallic or acid constituent found in the niobates and tantalates, see Dana's Text Book of Mineralogy, pages 489 to 493.

There are no uses for niobium or its compounds.

NITROGEN.

Occurrence.—Nitrogen is the characteristic non-metallic constituent of the nitrates, which, owing to their solubility, are of exceptional occurrence as minerals. Nitrogen is a constituent also of ammonia and its compounds, which occur rarely as minerals. Air is essentially a mixture of nitrogen and oxygen gases, in about the proportion, four volumes of nitrogen to one of oxygen.

Uses.—Nitric acid and its salts and ammonia compounds are extensively used in agriculture, and in chemical industries and laboratories. Explosives, such as gun powder, gun cotton, nitroglycerin, dynamite, material for fireworks, etc., contain either nitric acid derivatives or niter. Ammonia gas is used in artificial refrigerating plants. Nitrogen, either in nitrates or ammonia salts, or in refuse organic matter, is essential for plant nutrition, nitrogen of the air not being available for this purpose, except under conditions which do not ordinarily prevail.

Statistics.—Practically the world's supply of crude mineral material for making nitric acid and nitrates is sodium nitrate, the so-called *Chile saltpeter*, found in almost rainless regions in Chile and Bolivia. The amount produced there in 1901 was about 1,500,000 tons, much of it being used in fertilizers. Ammonia is almost wholly derived as bi-product from coke and gas ovens in which bituminous coal is distilled. The salt most in demand is ammonium sulphate, the larger part of which is used in fertilizers. The domestic production of ammonium sulphate in 1901 was 60,000 tons, the production of the world being about 500,000 tons. The price of commercial fertilizers is based upon the amounts of plant nutriment they contain. Of the three important nutritive elements, nitrogen, phosphorus and potassium, nitrogen heads the list, its value per pound being about 14.5 c.

OSMIUM.

Occurrence.—A very rare element found in iridosmium and in traces with the metals of the platinum group.

Uses.—The use of osmium for filaments for incandescent electric lights, in place of the ordinary carbon filaments, is causing a demand for this rare element. Osmium is worth about \$21 per troy ounce.

OXYGEN.

Occurrence.—Most minerals contain oxygen, the exceptions being the native elements; the sulphides, tellurides and selenides; the sulpho-salts (sulphantimonites, sulpharsenites) and the halogen-salt.

Uses.—Special importance is attached to certain higher oxides, notably those of manganese and lead, and to nitrates and chlorates which contain *available oxygen* for bringing about oxidations or obtaining oxygen gas. Oxygen and hydrogen gases are now made by the electrolysis of water, the oxygen, compressed in cylinders, being sold for use in medicine and for oxy-hydrogen blowpipes.

PALLADIUM.

Occurrence.—A rare metal of the platinum group, found native and in traces in native platinum.

PHOSPHORUS.

Occurrence.—Phosphorus is the characteristic non-metallic constituent of the phosphates; see Dana's Text Book of Mineralogy, pages 494 to 516.

Uses.—There are two modifications of the element phosphorus; the common colorless variety, cast generally in sticks, which finds limited uses in laboratories and various chemical industries, and the red, amorphous variety used to some extent in chemical industries, but extensively along with other substances in the manufacture of matches.

Phosphates are essential for plant nutrition and are important in the manufacture of commercial fertilizers; phosphorus, reckoned generally as phosphoric anhydride, P_2O_5 , ranking next to nitrogen in importance (compare page 41). The mineral phosphates mined for making fertilizers are either apatite, $Ca_4[CaF][PO_4]_3$, or so-called *phosphate rock*, which is a calcium phosphate closely related to apatite in chemical composition. Phosphate rock is generally treated with sulphuric acid to make the phosphoric acid soluble and thus available to the roots of plants. The inorganic material of the bones of mammals is essentially calcium phosphate, and phosphorus is contained in animal tissues and excreta; hence the extensive use of refuse animal matter and manure as fertilizers. Phosphoric acid and various phosphates are used in pharmaceutical preparations. The harmful influence of phosphorus, even in very small quantity, on iron and steel should be noted (see page 34).

Statistics.—The domestic production of phosphate rock, mined chiefly in Florida, Tennessee and South Carolina, amounted in 1901 to over 1,500,000 tons, valued at about \$5,500,000. From about one-third to one-half of the product was exported, mostly to Germany. The world's production of phosphate rock in 1900 was about 2,500,000 tons. The valuation of commercial fertilizers is based upon the amounts of plant nutriment they contain, which must be determined by chemical analysis. The three important constituents are phosphoric anhydride, P_2O_5 , nitrogen, and potash, K_2O . Soluble or available P_2O_5 is valued at a trifle over 3 c. per pound, or $62\frac{1}{2}$ c. per unit of 20 pounds (one per cent.) per ton. Insoluble phosphate rock, even if finely ground, is of very little agricultural value, unless treated with sulphuric acid so as to make the P_2O_5 available.

PLATINUM.

Occurrence.

Native Platinum, Pt, with some Fe and traces of rare platinum metals.
 Sperrylite, $Pt As_2$.

Uses.—Owing to its difficult fusibility and insolubility in acids, platinum, manufactured into wire, foil, crucibles, dishes, stills, and various forms of apparatus, is indispensable to the chemist and in certain chemical industries. There are numerous uses for it in connection with electricity: thus for making connections where a metal is needed which does not corrode; and fine platinum wire fused into glass is used in carrying the electric current to the incandescent filaments of electric lights. The incandescent thoria mantles of the Welsbach light are generally hung on platinum wire. Potassium chloro-platinate, $2 K Cl. Pt Cl_2$, is used to a considerable extent in photography. A noteworthy feature of the platinum industry is that demands for the metal are multiplying, with no appreciable increase in the supply.

Statistics.—The domestic production of platinum in 1901 was 1,400 ounces, valued at \$27,500, the supply coming almost wholly from gold placer deposits in California. The importation in 1901 was valued at over \$1,500,000. The world's supply of platinum comes from the Urals, where nearly 200,000 ounces are produced annually. The price of platinum is from \$20 to \$21 per ounce, nearly double what it was in 1895.

POTASSIUM.

*Occurrence.***SYLVITE**, $K\ Cl$.**CARNALLITE**, $K\ Mg\ Cl_3 \cdot 6\ H_2O$.**FELDSPAR, ORTHOCLASE and MICROCLINE**, $K\ Al\ Si_3\ O_8$.**LEUCITE**, $K\ Al\ [Si\ O_3]_2$.**Apophyllite**, and a few Zeolites.**MUSCOVITE**, $H_2\ K\ Al_3\ [Si\ O_4]_3$.**BIOTITE** and other Micas.Langbeinite, $K_2\ Mg_2\ [SO_4]_3$.**KAINITE**, $K\ Cl \cdot Mg\ SO_4 \cdot 3\ H_2O$.**SCHOENITE**, $K_2\ Mg\ [SO_4]_2 \cdot 6\ H_2O$.Polyhalite, $K_2\ Ca_2\ Mg\ [SO_4]_4 \cdot 2\ H_2O$.**Kalinite**, $K\ Al\ [SO_4]_2 \cdot 12\ H_2O$.**Alunite**, $K_2\ Al_6\ [OH]_{12}\ [SO_4]_4$.**Jarosite**, $K_2\ Fe_6\ [OH]_{12}\ [SO_4]_4$.

Uses.—Potash salts are essential for plant nutrition and are more largely employed in agriculture than in any single industry. The potash salts most in demand are as follows: The *chloride*, used in fertilizers and in making other potash salts; the *carbonate*, *bicarbonate* and *caustic potash*, used in making soft soaps and flint and Bohemian glass; the *nitrate*, niter, for making gun powder; the *chlorate*, for making matches and oxygen gas, and used also in medicine; the *cyanide*, employed in large quantities in the extraction of gold from ores; the *bromide* and *iodide*, used in medicine.

Statistics.—It is a noteworthy fact that no commercially important deposits of potash minerals have as yet been found in the United States. The world's supply of potash at the present time is mostly derived from deposits round about Stassfurt in Germany, though some potash is obtained from what was at one time almost the only source, the leaching of the ashes of plants, some from brines left over after separating common salt from sea water, and some from the washing of sheep's wool, the salty perspiration retained by the wool containing a rather large proportion of potash salts. The slow decay of the common rock making silicates, feldspars and micas, undoubtedly gives rise to the potash of soils, needed as plant nutriment, but attempt to get potash from feldspars on a commercial scale have failed, as the processes are so costly as not to be able to compete with the production in Germany.

The output of potash minerals in tons from the Stassfurt deposits in 1901 was as follows: Carnallite 1,860,000, schoenite and kainite 1,500,000, sylvite 190,000. Of the 3,500,000 tons, about 2,000,000 were used in the manufacture of various potash salts, and 1,500,000 in agriculture. The importation of pure potash salts into the United States in 1901 amounted to 113,000 tons, valued at \$4,300,000, about one-half being the chloride or *muriate*, as it is commonly called.

For agricultural purposes, potash, reckoned as K_2O , is worth about 4 to $4\frac{1}{2}$ c. per pound (compare nitrogen and phosphorus).

RHODIUM.

Occurrence.—This rare metal of the platinum group is found in native platinum, iridium and iridosmine.

RUBIDIUM.

Occurrence.—This rare alkali metal is found in small quantity in lepidolite, and in minute traces in a few other silicates and some mineral spring waters.

RUTHENIUM.

Occurrence.—This rare metal of the platinum group is found in laurite, Ru S_2 , and in iridosmine.

SELENIUM.

Occurrence.

Selen-Tellurium, Te with Se.

Guanajuatite, $\text{Bi}_2 \text{Se}_3$.

Clausthalite, Pb Se.

Naumannite, $(\text{Ag}_2, \text{Pb}) \text{Se}$.

Berzelianite, $\text{Cu}_2 \text{Se}$.

Eucairite, Cu Ag Se.

Crookesite, $(\text{Cu}, \text{Ti}, \text{Ag})_2 \text{Se}$.

Aguilarite, $\text{Ag}_2 \text{S} \cdot \text{Ag}_2 \text{Se}$.

Tiemannite, Hg Se.

Onofrite, Hg (S, Se).

Umangite, $\text{Cu}_3 \text{Se}_2$.

Chalcomenite, $\text{Cu Se O}_3 \cdot 2 \text{H}_2\text{O}$.

Uses.—As far as known there are no uses for this element except in the laboratory for making rare chemical preparations.

SILICON.

Occurrence.—Silicon is the characteristic non-metallic constituent of the silicates, salts of silicic acid, see Dana's Text Book of Mineralogy, pages 368 to 488. Silicon occurs also as oxide, quartz, agate, flint, chalcedony and tridymite, and as hydroxide, opal.

Uses.—There are no uses for the element silicon. In ordinary pig iron silicon occurs in varying proportions, up to 5 or 6 per cent. generally about 2 per cent., and plays an important rôle in the metallurgy of iron and steel. For use in steel metallurgy, ferro-silicon (Fe with 10% to 25% Si) is now made in electric furnaces. The burning of the silicon to Si O_2 gives an intense heat which is needed in certain operations. There are uses for various silicates which are noted either under the metallic constituents or under the heading, *Useful Minerals*. The uses of oxide of silicon in various forms, quartz, quartzite, sandstone, flint, etc., are given below.

Uses of Si O_2 .—White beach sand is composed almost wholly

and ordinary sand mostly of quartz, and has many uses, especially in making mortar, while very pure grades are used in the glass industry. Quartzite and sandstone consist of quartz grains more or less firmly united, and are quarried for building materials, flagstones, grindstones, millstones, whetstones and other uses. Well rounded beach pebbles put into revolving cylinders are used for pulverizing many substances. Ground quartz and flint are used extensively in the manufacture of pottery, to some extent as abrasive material in scouring soaps, marble cutting and sandpaper, and, when ground to impalpable powder and mixed with oils, as *wood filler* in finishing fine carpenter work. Pure transparent quartz is used for cutting into ornaments, rock-crystal dishes, vases, spheres, etc.; for making eye-glasses (pebbles) which are superior to glass in being harder; and for making prisms and optical preparations.

Opals, amethyst and smoky-quartz, and moss, banded and variously colored agates are used in jewelry. Mortars for the laboratory are made of agate.

Infusorial earth is a very fine earthy material consisting of microscopic silicious shells of vegetable organisms known as diatoms: The material, sold often as tripoli and electro-silicon, is used for polishing articles of metal, and in the manufacture of giant powder, when the infusorial earth is used as an absorbent for nitro-glycerin.

Statistics.—The domestic production of buhrstones and millstones in 1901 was valued at \$57,000. The stones, generally made from quartzite or conglomerate, are used for grinding grain, mineral-paint, fertilizers, cement rock, barites and other minerals, and come mostly from the Eastern Appalachian region in New York, Pennsylvania, Virginia and North Carolina. The value of grindstones was \$500,000, and of pulp-stones, used for grinding wood-pulp, \$19,000, the product coming mostly from Ohio, some from Michigan. The value of whetstones and scythe-stones was \$160,000, the finest whetstone, known as novaculite, coming from Arkansas.

The production of pure quartz for grinding is confined mostly to Connecticut and amounted in 1901 to 35,000 tons; about half of this, unground, was valued at \$18,000, the other half, ground, at \$120,000.

SILVER.

*Occurrence.***Native Silver**, Ag.

Amalgam, Ag with Hg.

Dyscrasite, Ag_6Sb .**Argentite**, Ag_2S .Hessite, Ag_2Te .Petzite, $(\text{Ag}, \text{Au})_2\text{Te}$.**Stromeyerite**, $\text{Ag}_2\text{S} \cdot \text{Cu}_2\text{S}$.**Sylvanite**, $\text{Ag Te}_2 \cdot \text{Au Te}_2$.Matildite, $\text{Ag}_2\text{S} \cdot \text{Bi}_2\text{S}_3$.Miargyrite, $\text{Ag}_2\text{S} \cdot \text{Sb}_2\text{S}_3$.**Pyrargyrite**, $3\text{Ag}_2\text{S} \cdot \text{Sb}_2\text{S}_3$.**Proustite**, $3\text{Ag}_2\text{S} \cdot \text{As}_2\text{S}_3$.**Stephanite**, $5\text{Ag}_2\text{S} \cdot \text{Sb}_2\text{S}_3$.**Polybasite**, $9\text{Ag}_2\text{S} \cdot \text{Sb}_2\text{S}_3$, Cu iso.
w. Ag.Pearceite, $9\text{Ag}_2\text{S} \cdot \text{As}_2\text{S}_3$, Cu iso. w. Ag.Polyargyrite, $12\text{Ag}_2\text{S} \cdot \text{Sb}_2\text{S}_3$.Argyrodite, $4\text{Ag}_2\text{S} \cdot \text{Ge S}_2$.Canfieldite, $4\text{Ag}_2\text{S} \cdot \text{Sn S}_2$, Ge iso.
w. Sn.**Cerargyrite**, Ag Cl.**Embolite**, Ag (Cl, Br).

Bromyrite, Ag Br.

Iodyrite, Ag I.

In addition to the foregoing there are argentiferous varieties of many minerals, notably those containing lead and copper, which are especially valuable as ores, as galena, chalcocite, bornite, chalcopyrite and tetrahedrite. It is difficult in many cases to decide whether the small amount of silver in argentiferous lead and copper minerals is truly isomorphous with the lead and copper, or due to traces of associated silver minerals mechanically mixed with them.

Uses.—The uses of silver for coin, for various domestic and ornamental objects, and for plating are well known. Generally an alloy is used instead of pure silver. The standard coin of the United States contains 9 parts of silver to one of copper. Silver salts are used extensively in photography and the nitrate in medicine for cauterization.

Statistics.—The domestic production of silver in 1901 was nearly 60,000,000 troy ounces, valued at \$35,000,000. The production of the several states in million ounces was about as follows: Colorado $18\frac{1}{2}$, Montana 13, Utah $10\frac{1}{2}$, Idaho $5\frac{1}{2}$, Arizona $2\frac{3}{4}$ and Nevada $1\frac{3}{4}$. The world's production amounted to 175,000,000 ounces. The value of the metal ranged from 55c. to 60c. per fine ounce.

Metallurgical.—In connection with the metallurgy of silver a few points are of importance: Owing to the price of silver, a small amount of the metal in an ore, expressed as per cent., is of considerable value. Thus an ore containing 0.34 per cent. Ag would yield 100 ounces per ton, which is far above the average run of silver ores. In assaying, the amount of silver is generally given as ounces per ton. The metallurgy of silver is intimately connected with that of lead, ores containing both metals being

smelted so that silver may be taken up by the lead (see page 36). In the smelting process, lime, Ca O, and oxides of iron and manganese add to the value of ores because of their quality as fluxes, and zinc, which scarcely ever fails, is especially harmful, as it interferes with the proper running of the furnaces.

SODIUM.

Occurrence.

HALITE, Na Cl.

CRYOLITE, $\text{Na}_3 \text{Al F}_6$.

Pachnolite, $\text{Na Ca Al F}_6 \cdot \text{H}_2\text{O}$.

Thomsonite, $\text{Na Ca Al F}_6 \cdot \text{H}_2\text{O}$.

Dawsonite, $\text{Na} [\text{Al} \cdot 2 \text{OH}] \text{CO}_3$.

Thermonatrite, $\text{Na}_2 \text{CO}_3 \cdot \text{H}_2\text{O}$.

Northupite, $\text{Na}_2 \text{Mg} [\text{CO}_3]_2 \cdot \text{Na Cl}$.

Natron, $\text{Na}_2 \text{CO}_3 \cdot 10 \text{H}_2\text{O}$.

Trona, $\text{Na}_2 \text{CO}_3 \cdot \text{H Na CO}_3 \cdot 2 \text{H}_2\text{O}$.

Pirssonite, $\text{Na}_2 \text{Ca} [\text{CO}_3]_2 \cdot 2 \text{H}_2\text{O}$.

Gay-Lussite, $\text{Na}_2 \text{Ca} [\text{CO}_3]_2 \cdot 5 \text{H}_2\text{O}$.

Eudidymite, $\text{H Na Be Si}_3 \text{O}_8$.

ALBITE, $\text{Na Al Si}_3 \text{O}_8$, and Albite—

Anorthite series of triclinic feldspars.

Aegirite, $\text{Na Fe} [\text{Si O}_3]_2$.

Jadeite, $\text{Na Al} [\text{Si O}_3]_2$.

Pectolite, $\text{H Na Ca}_2 [\text{Si O}_3]_2$.

Glaucophane, $\text{Na Al} [\text{Si O}_3]_2 \cdot (\text{Fe, Mg}) \text{Si O}_3$.

Eudyalite, $\text{Na}_{12}(\text{Ca, Fe})_6 \text{Cl}(\text{Si, Zr})_{20} \text{O}_{52}?$

NEPHELITE, approximately

Na Al Si O_4 .

Cancrinite, $\text{H}_6 \text{Na}_6 \text{Ca} [\text{Na CO}_3]_2 \text{Al}_3 [\text{Si O}_4]_9$.

Sodalite, $\text{Na}_4 [\text{Al Cl}] \text{Al}_2 [\text{Si O}_4]_3$.

Haüynite, $(\text{Na}_2, \text{Ca})_2 [\text{Al} \cdot \text{Na SO}_4] \text{Al}_2 [\text{Si O}_4]_3$.

Noselite, $\text{Na}_4 [\text{Al} \cdot \text{Na SO}_4] \text{Al}_2 [\text{Si O}_4]_3$.

Lazurite, $\text{Na}_4 [\text{Al} \cdot \text{Na S}_3] \text{Al}_2 [\text{Si O}_4]_3$.

WERNERITE or **SCAPOLITE**, $\left\{ \begin{array}{l} \text{Ca}_4 \text{Al}_6 \text{Si}_6 \text{O}_{25} \\ \text{Na}_4 \text{Al}_3 \text{Si}_9 \text{O}_{24} \text{Cl} \end{array} \right.$

ANALCITE, $\text{Na Al} [\text{Si O}_3]_2 \cdot \text{H}_2\text{O}$.

NATROLITE, $\text{Na}_2 \text{Al}_2 \text{Si}_3 \text{O}_{10} \cdot 2 \text{H}_2\text{O}$.

Paragonite, $\text{H}_2 \text{Na Al}_3 [\text{Si O}_4]_3$.

Natrophilite, Na Mn PO_4 .

Beryllonite, Na Be PO_4 .

Durangite, $\text{Na} [\text{Al F}] \text{As O}_4$.

SODA-NITER, Na NO_3 .

Darapskite, $\text{Na NO}_3 \cdot \text{Na}_2 \text{SO}_4 \cdot \text{H}_2\text{O}$.

BORAX, $\text{Na}_2 \text{B}_4 \text{O}_7 \cdot 10 \text{H}_2\text{O}$.

Ulexite, $\text{Na Ca B}_5 \text{O}_9 \cdot 8 \text{H}_2\text{O}?$

Thenardite, $\text{Na}_2 \text{SO}_4$.

Glauberite, $\text{Na}_2 \text{Ca} [\text{SO}_4]_2$.

Sulphohalite, $2 \text{Na}_2 \text{SO}_4 \cdot \text{Na Cl} \cdot \text{Na F}$.

Hanksite, $9 \text{Na}_2 \text{SO}_4 \cdot 2 \text{Na}_2 \text{CO}_3 \cdot \text{K Cl}$.

Mirabilite, $\text{Na}_2 \text{SO}_4 \cdot 10 \text{H}_2\text{O}$.

Natrojarosite, $\text{Na}_2 \text{Fe}_6 [\text{OH}]_{12} [\text{SO}_4]_4$.

In addition to the foregoing compounds sodium is found in variable quantities in a number of common minerals where it plays the rôle of an isomorphous constituent.

Uses.—There is some demand for metallic sodium in chemical industries and laboratories, and it is now generally made by electrolytic methods. Halite, or rock salt, is used in enormous quantities in the manufacture of soda-ash, caustic-soda and various soda salts, in addition to its uses in every household, and for packing and preserving meats and fish. Sodium hydroxide, caustic-soda or lye, has various uses but is chiefly employed in the manufacture of soap. Crude sodium carbonate or soda-ash is used in the manufacture of glass and in the preparation of sodium compounds. Crystallized sodium carbonate or sal-soda, $\text{Na}_2 \text{CO}_3 \cdot 10 \text{H}_2\text{O}$, is

used for cleansing and is mixed with powdered soaps for giving added cleansing quality. Sodium bicarbonate, or baking soda, H Na CO_3 , is used in every household, and extensively in making baking powders and in medicine.

The ordinary glaze on cheap stoneware and tile is produced by throwing salt into kilns where the ware is burned. The salt volatilizes and reacts with various silicates of the ware, giving rise to a glaze of fused sodium silicate. This glaze is quite different from that produced by feldspar on more costly ware.

Statistics.—Common salt or halite is practically the basis of all soda industries, consequently of glass and soap making. The domestic production of salt in 1901 was 20,500,000 barrels of 280 pounds, or nearly 3,000,000 tons, valued at the works at about \$6,500,000. The leading salt-producing states and their approximate production in million barrels are as follows: Michigan $7\frac{3}{4}$, New York $7\frac{1}{4}$, Kansas 2 and Ohio 1. At the present time the United States is the leading salt-producing country of the world, and furnishes about one-fourth of the total production. Salt is worth about \$1.50 to \$2 per barrel in New York.

The domestic production of soda (soda ash, caustic and bicarbonate) in 1901 was nearly 500,000 tons. Factory prices for 100 pounds of the various products are about as follows: Bicarbonate \$1.10, caustic \$1.95, soda ash 85c., sal soda 55c.


Sodium bicarbonate produced from natural deposits in the arid regions of California and Nevada amounted in 1901 to 15,000 tons, valued at \$200,000, and considerable soda is made from cryolite brought from Greenland, but the total amounts from these sources are small compared with the production from common salt.

STRONTIUM.

Occurrence.

STRONTIANITE, Sr CO_3 .

Brewsterite,



Hamlinite, $[\text{Sr. OH}][\text{Al. 2 OH}]_3\text{P}_2\text{O}_7$.

CELESTITE, Sr SO_4 .

Uses.—Strontium oxide and hydroxide are used in refining beet sugar, and other salts, especially the nitrate, $\text{Sr}[\text{NO}_3]_2$, are employed for making red fire in pyrotechnics.

Statistics.—There is practically no production of strontium minerals in the United States, though they would command good prices. The supply of strontium salts comes almost wholly from Germany, and as an indication of their value strontium nitrate is quoted in New York at about \$140 per ton.

SULPHUR.

Occurrence.—Sulphur is found native, which is one of its most important occurrences from an economic standpoint. In combination with metals sulphur forms sulphides and sulphy-salts (sulphantimonites, etc.), many of which are of great importance as ores, see Dana's Text Book of Mineralogy, pages 281 to 316. Sulphur in combination with the metals and oxygen forms sulphates, see Dana, pages 523 to 538.

Uses.—Sulphur (brimstone) and pyrite, Fe S_2 , are used in the manufacture of sulphuric acid (oil of vitriol) which is employed in numerous chemical and metallurgical industries, in the manufacture of fertilizers and in the refining of petroleum. Sulphur dioxide, formed by burning sulphur, is used in enormous quantity in the preparation of wood pulp for paper stock, also to some extent as an antiseptic and disinfectant, and for bleaching silk, wool and straw materials. The element sulphur is used in vulcanizing rubber, in making gun powder, for tipping matches, and in a finely divided condition (flowers of sulphur) in medicine.

Statistics.—The domestic production of sulphur in 1901 was nearly 7,500 tons, valued at \$225,000, the supply coming from Nevada, Idaho, Utah and Louisiana. There were also produced 260,000 tons of pyrite, estimated to contain 115,000 tons of sulphur, and valued at about \$1,000,000. Thus the total domestic production of sulphur was about 122,500 tons. The importation of sulphur in 1901 amounted to nearly 200,000 tons, valued at \$3,250,000, and of pyrite 450,000 tons valued at \$1,400,000. Estimating the sulphur in the pyrite as 210,000 tons, the total importation of sulphur was about 400,000 tons. The world's production of sulphur (brimstone) is about 600,000 tons, more than 90 per cent. coming from the island of Sicily.

Most of the sulphur (brimstone) consumed in the United States is used in the manufacture of paper stock. The pyrite is used in the manufacture of sulphuric acid, consumed largely by chemical and agricultural companies and by the Standard Oil Company.

TANTALUM.

Occurrence.—The rare element tantalum is found in connection with niobium in the niobates and tantalates, see Dana's Text Book of Mineralogy, pages 489 to 493. There are no uses for tantalum.

TELLURIUM.

Occurrence.

Native Tellurium, Te.
 Selen-tellurium, (Te, Se).
 Tetradyomite, $\text{Bi}_2 \text{Te}_2 \text{S}$.
 Hessite, $\text{Ag}_2 \text{Te}$.
 Petzite, $(\text{Ag}, \text{Au})_2 \text{Te}$.
 Altaite, Pb Te .
 Coloradoite, Hg Te .
 Melonite, $\text{Ni}_2 \text{Te}_3$.
 Rickardite, $\text{Cu}_4 \text{Te}_3$.

Sylvanite, Au Ag Te_4 .
 Krennerite, Au Te_2 } with some Ag.
Calaverite, Au Te_2 } iso. w. Au.
 Nagyagite, $\text{Au}_2 \text{Sb}_2 \text{Pb}_{10} \text{Te}_6 \text{S}_{15}?$
 Tellurite, Te O_2 .
 Montanite, $[\text{Bi. 2 OH}]_2 \text{Te O}_4$.
 Durdenite, $\text{Fe}_3 [\text{Te O}_3]_3 \cdot 4 \text{H}_2\text{O}$.
 Emmonsite, hydrated ferric tellurite.

Uses.—There is no demand for tellurium, except a very limited one for making rare laboratory preparations.

THALLIUM.

Occurrence.

Crookesite, $(\text{Cu}, \text{Tl}, \text{Ag})_2 \text{Se}$.

Lorandite, Tl As S_2 or $\text{Tl}_2 \text{S. As}_2 \text{S}_3$.

Uses.—Thallium is occasionally used in the laboratory for making monochromatic green light, and also rare chemical preparations.

THORIUM.

The occurrences and uses of this rare earth metal are noted on page 30, under Cerium.

TIN.

Occurrence.

Stannite, $\text{Cu}_2 \text{Fe Sn S}_4$.
 Canfieldite, $\text{Ag}_4 (\text{Sn}, \text{Ge}) \text{S}_6$.
 Cyndrite, $\text{Pb}_6 \text{Sb}_2 \text{Sn}_6 \text{S}_{21}$.

Franckeite, $\text{Pb}_5 \text{Sb}_2 \text{Sn}_2 \text{S}_{12}$.
CASSITERITE, Sn O_2 or Sn Sn O_4 .
 Nordenskiöldine, $\text{Ca Sn [B O}_3\text{]}_2$.

In addition to the foregoing minerals small quantities of tin are often met with in niobates, tantalates and tungstates.

Uses.—The chief use of tin is for coating or tinning metals, especially iron, thus making what is commonly called *sheet tin* used for roofing and tin ware. The silvering of mirrors is accomplished by covering glass with an amalgam of tin and mercury. Tin is used in making alloys: solder, which contains tin and lead; and bell metal and bronze, which contain copper and tin. Artificial tin oxide is used as a polishing powder; stannic chloride as a mordant in dyeing.

Statistics.—There is practically no production of tin ore in the United States, though some has been mined in the Black Hills, South Dakota. The importation of metallic tin amounted, in 1901, to 37,000 tons, valued at \$19,000,000. The world's production of tin amounted to about 100,000 tons, derived from the following sources: Straits of Malacca (Malay Peninsular) 60,000; Banka and Billiton, near Sumatra, 20,000; Bolivia 11,000, England 4,500, Australia 3,500. The price of tin in New York is from 25c. to 30c. per pound.

TITANIUM.

Occurrence.

ILMENITE, titaniferous iron, Fe Ti O_3 , containing also Mg Ti O_3 and $\text{Fe}_2 \text{O}_3$.

Pseudobrookite, $2 \text{Fe}_2 \text{O}_3 \cdot 3 \text{Ti O}_2$.

RUTILE, Ti O_2 or Ti Ti O_4 .

Octahedrite, Ti O_2 .

Brookite, Ti O_2 .

Schorlomite, $\text{Ca}_3 (\text{Fe, Ti})_2 [(\text{Si, Ti}) \text{O}_4]_3$.

TITANITE, Ca Ti Si O_6 .

Astrophyllite,

$(\text{Na, K})_4 (\text{Fe, Mn})_4 \text{Ti} [(\text{Si O}_4)]_4$.

Perovskite, Ca Ti O_3 .

Titanium is found in numerous niobates and tantalates, especially aeschenite, polymignite, euxenite and polycrase, and in small quantities in many silicates.

Uses.—Titanium has long been used for imparting a yellow color to porcelain, employed mostly by dentists in coloring false teeth, of which it is estimated that over 8,000,000 are made annually in the United States. Steel containing a little titanium has been found to have a high limit of elasticity and great ductility, hence ferro-titanium alloys are now made by means of the electric furnace for use in the steel industry.

Many iron ores are titaniferous and as yet have proved practically valueless, as they are too refractory to be smelted successfully in blast-furnaces.

Statistics.—The amount of rutile produced in Virginia in 1901 was 44,000 pounds, valued at \$4,500. Previously the total domestic production has never exceeded 300 pounds, but the quality has been such as to demand as high a price as \$4 per pound.

TUNGSTEN.

Occurrence.

Tungstite, W O_3 .

WOLFRAMITE, $(\text{Fe, Mn}) \text{W O}_4$.

Hübnerite, Mn W O_4 .

Raspite, Pb W O_4 .

Scheelite, Ca W O_4 .

Cuprotungstite, $(\text{Cu, Ca}) \text{W O}_4$.

Stolzite, Pb W O_4 .

Reinrite, Fe W O_4 .

Small quantities of tungsten are met with in several of the rare niobates and tantalates.

Uses.—The element tungsten, and an alloy with iron, ferro-tungsten, are used in the production of self-hardening tungsten steel, also for giving toughness to a copper aluminium alloy used for propeller blades. Sodium tungstate is used for making certain colors "fast" in dyeing cotton goods, and is applied to fabrics to make them noninflammable. A little tungstic oxide is used for coloring glass. Calcium tungstate is used in Röntgen-ray apparatus on account of its phosphorescence.

Statistics.—The domestic production of concentrated tungsten ores in 1901 was 180 tons, valued at \$27,500. The ore was mostly wolframite from Colorado, some from South Dakota.

URANIUM.

Occurrence.

Uranothalite, $\text{Ca}_2 \text{U} [\text{CO}_3]_{11} \cdot 10 \text{H}_2\text{O}$.	Uraninite, pitchblende, UO_3 ,
Torbernite, $\text{Cu} [\text{UO}_2]_2 [\text{PO}_4]_2 \cdot 8 \text{H}_2\text{O}$.	UO_2 , ThO_2 , PbO , He , etc.?
Zeunerite, $\text{Cu} [\text{UO}_2]_2 [\text{AsO}_4]_2 \cdot 8 \text{H}_2\text{O}$.	Gummite, $\text{UO}_3 + \text{H}_2\text{O}$ and other ox-
Autunite, $\text{Ca} [\text{UO}_2]_2 [\text{PO}_4]_2 \cdot 8 \text{H}_2\text{O}$.	ides.
Uranophane, $\text{Ca U}_2 \text{Si}_2 \text{O}_{11} \cdot 6 \text{H}_2\text{O}$.	Carnotite, $\text{K}_2 [\text{UO}_2]_2 [\text{VO}_4]_2 \cdot 3 \text{H}_2\text{O}?$

Uses.—Uranium compounds are used for coloring glass and as pigments for painting on porcelain. Uranium minerals have special interest at the present time as they contain radium, helium, thorium and other rare elements which are receiving unusual attention from chemists.

Statistics.—About 350 tons of uranium ore, carnotite, valued at \$100,000, were mined in Colorado in 1901. The product was mostly exported to Europe for treatment.

VANADIUM.

Occurrence.

Roscoelite,	Descloizite (Pb, Zn) $_2 [\text{OH}] \text{VO}_4$.
$\text{H}_8 \text{K}_2 (\text{Mg}, \text{Fe}) (\text{Al}, \text{V})_4 [\text{SiO}_3]_{12}?$	Volborthite,
Ardennite, $\text{H}_8 \text{Mn}_4 \text{Al}_4 \text{V Si}_4 \text{O}_{28}?$	$(\text{Cu}, \text{Ca}, \text{Ba})_3 [\text{OH}]_3 \text{VO}_4 \cdot 6 \text{H}_2\text{O}?$
Pucherite, Bi V O_4 .	Carnotite, $\text{K}_2 [\text{U O}_2]_2 [\text{V O}_4]_2 \cdot 3 \text{H}_2\text{O}?$
Vanadinite, $\text{Pb}_4 [\text{Pb Cl}] [\text{VO}_4]_3$.	

Uses.—It is claimed that the addition of a little vanadium to steel increases enormously its tensile strength and elastic limit. Metavanadic acid, HVO_3 , is a fine yellow pigment known as vanadium bronze. Vanadium oxide is used as mordant in dyeing.

Statistics.—Considerable vanadium is obtained from the carnotite deposits of Colorado. See Uranium.

YTTRIUM.

Occurrence.—For the occurrence of this rare metal, see Cerium and the Rare Earth Metals, page 30.

ZINC.

Occurrence.

SPHALERITE, Zn S , also $(\text{Zn, Fe}) \text{S}$.

Wurtzite, Zn S .

Zincite, Zn O .

Cahnite, $\text{Zn Al}_2 \text{O}_4$.

Franklinite,

$(\text{Fe, Zn, Mn}) (\text{Fe, Mn})_2 \text{O}_4$.

SMITHSONITE, Zn CO_3 .

Aurichalcite,

$(\text{Zn, Cu})_5 [\text{OH}]_6 [\text{CO}_3]_2$.

Hydrozincite, $\text{Zn}_3 [\text{OH}]_4 \text{CO}_3$.

Hardystonite, $\text{Ca}_2 \text{Zn Si}_2 \text{O}_7$.

Willemite, $\text{Zn}_2 \text{SiO}_4$, Mn iso. w. Zn.

CALAMINE, $\text{H}_2 [\text{Zn}_2 \text{O}] \text{SiO}_4$.

Clinohedrite, $\text{H}_2 [\text{Ca Zn O}] \text{SiO}_4$.

Adamite, $\text{Zn}_2 [\text{OH}] \text{AsO}_4$.

Hopeite, $\text{Zn}_3 [\text{PO}_4]_2 \cdot \text{H}_2\text{O}?$

Coslarite, $\text{Zn SO}_4 \cdot 7 \text{H}_2\text{O}$.

Uses.—The chief uses for metallic zinc, commonly known as spelter, are for galvanizing iron; making brass, an alloy of copper and zinc; and making parts of telegraph and storage batteries. There are also numerous uses for sheet zinc. Zinc oxide or zinc white, either alone or mixed with white lead, is extensively used for making paint, and is also compounded with rubber. Zinc chloride is used as preservative, many railroad ties being treated with it. Zinc sulphate has numerous uses, in dyeing and in medicine.

Statistics.—The domestic production of zinc or spelter in 1901 was 140,000 tons, valued at about \$11,000,000, the ore being mostly sphalerite from Kansas and Missouri. At the present time there is considerable activity in the treatment of the zinc-lead-silver ores of Colorado and other western states, in which formerly the zinc was a waste product. The production of zinc oxide in 1901 was 46,500 tons, valued at \$3,720,000, made mostly in New Jersey and Pennsylvania. About one-fourth of the world's production of zinc is obtained in the United States. The price of zinc in 1901 was about 4 c. per pound, but it rose during 1902 to nearly $5\frac{1}{2}$ c.

ZIRCONIUM.

Occurrence.

Baddeleyite, Zr O_2 .

Wöhlerite $(\text{Ca, Na}_2) (\text{Si, Zr}) \text{O}_3$, with
 $(\text{Ca, Na}_2) \text{Nb}_2 \text{O}_6$.

Eudialyte,

$\text{Na}_{13} (\text{Ca, Fe})_6 \text{Cl} (\text{Si, Zr})_{20} \text{O}_{52}?$

Catapleiite, $\text{H}_4 (\text{Na}_2, \text{Ca}) \text{Zr Si}_3 \text{O}_{11}$.

ZIRCON, Zr SiO_4 .

Polymignite, Nb, Ti, Zr, Ce, Fe,
Ca, etc.?

Uses.—Oxide of zirconium glows when heated, but its use for incandescent lights is very limited.

USEFUL MINERALS.

Under this heading a number of minerals are given which have not been included in foregoing pages because their uses are not suggested by the constituents they contain. For convenience an alphabetical arrangement is adopted.

ABRASIVES.

Minerals possessing superior hardness are used for cutting, grinding and polishing other substances, and are known commercially as abrasives. They enter the market in grains of various sizes, down to dust; are made up into special shapes demanded by the trade, generally wheels; and are cemented to belting, cloth and paper. The minerals used are as follows:

Diamond, hardness 10.—Crystals and grains of diamond, when firmly imbedded in steel tubes and wheels, are used for drilling and sawing, and diamond dust is used on wheels and laps for grinding and polishing. The value of diamond dust imported into the United States in 1901 was over \$800,000. Carbonado or black diamond, found only in Brazil, is the most effective of all abrasives and is valued at from \$50 to \$55 per carat, equivalent to \$7,000 per ounce avoirdupois. The glazier's diamond is always a crystal with natural faces.

Corundum and Emery.—Corundum is crystallized Al_2O_3 , having a hardness of 9. Emery is a commercial term for corundum more or less impure from admixture with oxides of iron. The domestic production of corundum and emery in 1901 was a little over 4,000 tons, valued at nearly \$150,000. Corundum is produced mostly in western North Carolina and best grades are worth from 7 c. to 10 c. per pound. Emery, the chief product, is mostly produced at Chester, Mass., and Peekskill, N. Y., and brings from 2 c. to 5 c. per pound according to quality. The importation of emery, mostly from Turkey, is 12,000 tons annually, valued at about \$250,000.

Artificial corundum is now being manufactured in electric furnaces from bauxite. Another artificial abrasive is carborundum, SiC , having a hardness about like that of corundum. Carborundum is made in electric furnaces from coke and sand, and the production in 1901 was nearly 4,000,000 pounds, valued at about 8 c. per pound.

Garnet, hardness 7 to 7.5.—The domestic production in 1901 amounted to nearly 4,500 tons, valued at over \$150,000. The material came mostly from near Ticonderoga, N. Y., some from Connecticut, Pennsylvania and North Carolina. The average price per ton was \$35.50, best grades bringing as high as \$60.

Quartz, hardness 7.—The various uses of this mineral are noted on pages 45 and 46.

Pumice.—This is a name given to volcanic ash, used in lump and powder for polishing. The commercial product comes mostly from the island of Lipari, north of Sicily, and the value of the product annually imported into the United States is from \$50,000 to \$65,000.

ASBESTOS.

Asbestos is a name given to several fibrous minerals, generally tremolite, a variety of hornblende; anthophyllite, a closely related mineral; and chrysotile, a variety of serpentine. The material is used largely as a nonconductor of heat for covering boilers and steam pipes, and packing safes. Fine-fibrous varieties, generally chrysotile, are woven into cloth, twine and rope, and made up into paper, felt, board, washers and various shapes. The domestic production of asbestos in 1901, mostly tremolite from Georgia, was about 750 tons, valued at \$13,500. The bulk of best quality chrysotile-asbestos comes from Canada, though some is produced in the United States. There is a large domestic production of artificial material known as "mineral wool," made from furnace slag.

CEMENT.

Cements are products obtained by burning limestones containing proper amounts of argillaceous (clay) material, or finely ground mixtures of limestone and clay. The industry is one of great magnitude, the domestic production in 1901 being 20,000,000 barrels of from 300 to 400 pounds, valued at over \$15,000,000. The importations amounted to nearly 1,000,000 barrels, valued at \$1,300,000.

CLAY.

Clays are essentially hydrated silicates of aluminium, resulting from the decomposition of other minerals, especially feldspars. The decomposition of feldspar alone, *in situ*, gives rise to a pure white mineral, kaolinite, $H_2 Al_2 Si_2 O_9$. Ordinary clays are variously colored, and consist of kaolinite compounded with other

materials resulting from the decomposition of rocks, and they are commonly found in secondary deposits where they have been laid down as sediments from water. Most clays have the property of becoming plastic when mixed in proper proportions with water, so that they may be moulded, pressed and wrought into shapes, hence their use in the manufacture of brick, terra-cotta, tile, earthenware and pottery. The importance of the domestic clay industries is evident from the values of the several products produced in 1901, as follows: Brick \$50,000,000; fire brick \$10,000,000; paving and vitrified brick \$5,500,000; sewer and drain tile \$6,500,000; stoneware, terra-cotta and other ware \$15,000,000; pottery \$22,000,000, a total of nearly \$110,000,000. The value of the domestic production of kaolinite for the pottery industry amounted to nearly \$600,000, and a somewhat greater quantity was imported. Feldspar, quartz and fine qualities of clay also entered into the composition of pottery.

FELDSPAR.

Feldspar is mined almost exclusively for use in the porcelain and chinaware industry. It is compounded with kaolin and other materials for making the body of the ware, and when applied to the outside and fused it produces the glaze. Potash feldspar, orthoclase or microcline, $K Al Si_3 O_8$, is the kind generally used, though albite, $Na Al Si_3 O_8$, is probably equally good. To be of satisfactory quality feldspar must be practically free from quartz, mica and oxides of iron, and when ground is worth from \$8 to \$9 per ton. The domestic production of feldspar in 1901 was about 35,000 tons, valued at \$220,000, the supply coming from Pennsylvania, Maryland, Connecticut and New York.

Feldspar is of importance agriculturally, for undoubtedly much of the available potash in soils has resulted from the slow decomposition of orthoclase.

FLINT.

Flint is a recognized variety of silica, related to chalcedony, usually of dull gray, brown or black color. In commerce the ordinary varieties of quartz are commonly called flint; see Silica, pages 45 and 46.

FULLER'S EARTH.

Fuller's earth is a fine clay-like material, which lacks the plasticity of ordinary clay, and is remarkable for its absorbent qualities. It was formerly used by fullers as an absorbent for grease in cleansing cloth, but its chief use at the present time is as

a substitute for boneblack in bleaching and clarifying cottonseed and mineral oils. The domestic production in 1901, chiefly from Florida, was 14,000 tons, valued at nearly \$100,000. The importation was over 10,000 tons, valued at \$80,000.

GARNET.

Garnet is used to a considerable extent as an abrasive, page 56, and commonly as a gem mineral, see page 59.

GEM MINERALS OR PRECIOUS STONES.

NOTE.—For ornamental stones, other than gems, see page 63.

Gem minerals must satisfy the following conditions: (1) They must be hard, so as to withstand without scratching or defacement the wear to which they are subjected. (2) They must have a pleasing color, or be white or colorless. (3) If transparent, they should have a high index of refraction, on which largely depend their flash, brilliancy and beauty. Gems are generally sold by the carat, less often by the pennyweight. The international carat is equal to 205 milligrams, or about 1-138th of an ounce avoirdupois, and to give an idea of this weight a one-carat diamond, cut round in the customary form of a brilliant, is a stone of fair size, measuring 6.25 mm. in diameter and 4 mm. in depth. The values of gems are subject to great variation; thus, a gem of exceptional perfection in color and lustre will command a price far above that of a stone of the same kind but of only fair quality; moreover, rarity and size are important factors. Bearing variation in mind, however, an attempt will be made in the following pages to convey some idea of the relative values of different gems by giving for each the approximate price of a stone of best quality and of one-carat weight.

The minerals generally used as gems are as follows:

Agate.—A translucent, banded, variously colored variety of quartz or chalcedony. Inexpensive.

Amethyst.—A transparent purple or bluish-violet variety of quartz. Comparatively inexpensive, except when large and of unusually fine quality or color.

Aquamarine.—A name applied to transparent pale green or bluish-green varieties of beryl. Green gems of one-carat size are valued at from \$3 to \$5; those of rare blue color as high as \$30.

Beryl, $\text{Be}_3 \text{Al}_2 [\text{SiO}_3]_6 + \text{a little } \text{H}_2\text{O}$.—Aquamarine and emerald are names by which light and dark green gem varieties of this mineral are known. Some very beautiful gems are cut from beryl of yellow color, sometimes called golden beryl. A one-carat golden beryl would be valued at from \$3 to \$5.

Chrysoberyl, $\text{Be Al}_2 \text{O}_4$.—Handsome gems are cut from transparent yellowish or yellowish green crystals of this mineral, and a one-carat stone is valued at from \$3 to \$5. A far rarer and more highly prized variety, which is green by day and garnet-red by lamp light, is known as Alexandrite, and commands a value of from \$50 to \$60 for a one-carat stone. Some translucent stones when cut with rounded surfaces, *en cabochon*, exhibit a beautiful opalescent radiation or chatoyant effect, when they are called cat's eye. Other minerals, quartz, corundum, feldspar and tourmaline, likewise give chatoyant effects, but chrysoberyl is generally considered as the true or oriental cat's eye. A good cat's eye of one-carat weight may be valued at \$50 or more.

Chrysolite, $(\text{Mg}, \text{Fe})_2 \text{SiO}_4$.—Transparent green or yellowish green varieties of this mineral yield handsome gems, which are generally known and sold as peridot. A one-carat stone is valued at about \$5.

Chrysoprase.—This is a name given to a translucent apple-green variety of quartz or chalcedony. The stone is inexpensive.

Diamond, C .—A mineral remarkable for its brilliancy and hardness; index of refraction, $n = 2.42$, hardness = 10. Colorless or transparent white stones are most in demand, but variously colored ones are used, straw-yellow being most common. An ordinary white brilliant of one-carat weight and of good quality is valued at from \$150 to \$175, while extra blue-white and fancy colored stones of like weight may be valued as high as \$400 to \$500. One-carat diamonds of the ordinary straw-yellow color are worth about \$50.

Emerald.—This is a name given to deep green varieties of beryl, the color being due supposedly to traces of chromium. Because of the rarity and great beauty of this stone, a fine gem of one-carat weight may be valued at from \$800 to \$1,000, depending upon perfection.

Garnet.—Various kinds of garnet, page 4, are used as gems, and the stones exhibit a great variety of colors. Pyrope and almandite are the kinds most often used and the colors are gen-

erally deep tones of red. Good stones are valued up to \$5 per carat. A variety intermediate between pyrope and almandite, known as rhodolite, has a delicate rose to purplish red color, and a one-carat stone may be valued as high as \$15. Another very beautiful and still more costly garnet is a variety of andradite, known as demantoid, having a grass-green to emerald-green color.

Jasper.—This is a name applied to quartz which is colored red by oxide of iron. The stone is an inexpensive one, used to a limited extent in jewelry.

Lazurite or Lapis-Lazuli, $\text{Na}_4[\text{Al} \cdot \text{Na S}_3] \text{Al}_2[\text{SiO}_4]_3$.—A translucent stone of deep ultramarine blue color, only occasionally used in jewelry and not expensive.

Moonstone.—Some feldspars, when cut with rounded surfaces, show chatoyancy and delicate variations of color and are known as *moonstones*. The kind used in jewelry is generally potash feldspar, orthoclase, although other feldspars show a play of colors, notably labradorite and a variety of albite-oligoclase called *peristerite*. Moonstones of one-carat size are valued at about \$3.

Opal.—This is an amorphous form of silica, differing from quartz in having a much lower specific gravity and containing considerable hydroxyl, equivalent generally to from 3 per cent. to 9 per cent. of water. Opals are translucent to transparent, and many varieties are remarkable for their magnificent play of colors, which on some stones are soft and subdued, on others fiery and brilliant. Opals are generally cut *en cabochon*, and stones of one-carat size are valued up to about \$6. Stones of large size and exceptionally fine quality are very highly prized.

Peridot.—See chrysolite.

Pyroxene.—A transparent variety of pyroxene, known as *diopside*, is occasionally cut as a gem. The color is generally some light shade of green, and is very pleasing, but the stone is almost too soft to be serviceable. A stone of one-carat size is valued at from \$2 to \$3.

Quartz.—Various transparent varieties of this mineral are cut rather as ornaments than as gems. The kinds generally used are colorless rock crystal, amethyst, smoky quartz or cairngorm stone, and yellow quartz, which is sometimes called false topaz.

Ruby.—This is a name given to red varieties of corundum. A ruby of fine quality and color is one of the rarest and most beautiful of gems, and a stone of one-carat weight may be valued as high as \$1,500.

Sapphire.—This is a name by which the transparent, blue variety of corundum is generally known, although the name is also applied to gem corundums of various colors. A one-carat sapphire of fine blue color is valued at from \$80 to \$100, while fancy colored stones other than blue range from \$6 to \$30.

Spinel, $\text{Mg Al}_2\text{O}_4$.—This mineral exhibits a variety of colors, deep red, rose-red, orange and violet. The red varieties are known as *spinel-ruby*, but are inferior to the true corundum ruby. A one-carat gem of fine quality may be valued as high as \$200.

Spodumene, $\text{Li Al [Si O}_3\text{]}_2$.—Gems of yellowish or pale yellowish-green color are most common and are inexpensive. An emerald-green variety known as *hiddenite*, found in North Carolina, is very choice, and a one-carat stone would be worth about \$150.

Topaz, $[\text{Al (F, OH)}]_2 \text{SiO}_4$.—This mineral may be colorless, straw-yellow, wine-yellow, bluish or greenish. The kind generally used for gems is yellow. The color of some yellow crystals is changed to a delicate rose by heating. Gems of one-carat size are valued at about \$5 to \$10.

Tourmaline, a complex boro-silicate of aluminium and other bases.—This mineral exhibits a greater variety of colors than almost any other. As gems, green is the prevailing color, though delicate rose, wine-red (rubellite), blue and brown varieties are cut. Gems of one-carat size are valued about as follows: Green, \$5; rose, \$20; rubellite, \$30 to \$40.

Turquoise, a basic phosphate of aluminium, colored by a little copper.—This is a non-transparent stone, of robin's-egg blue or bluish-green color, generally cut *en cabochon*. A one-carat stone is valued at about \$10.

Zircon, Zr Si O_4 .—Transparent zircon exhibits a great variety of colors, from almost colorless to yellow, orange, red and brownish red. One-carat stones are valued at from \$10 to \$30.

Statistics.—The production of precious stones in the United States is comparatively small, their total value in 1901 amounting to less than \$300,000, while the importation at the port of New York alone is given as \$22,500,000. For 1901 the valuations of

the several domestic products which are worthy of special note are as follows: Turquoise, mostly from New Mexico, Nevada and Arizona, \$118,000; sapphires, mostly from Montana, \$90,000; garnet, mostly rhodolite from North Carolina, \$22,000; tourmaline, from Maine and California, \$15,000; beryl, aquamarine and emerald, from North Carolina, \$6,000.

GRANITE.

Granite is a crystalline rock consisting chiefly of feldspar and quartz, with biotite, hornblende and other minerals as accessories. It is extensively used for building and monumental work, for paving blocks, and as crushed stone for railroad ballast and road making. The value of the domestic production in 1901 for all purposes was estimated at \$16,000,000.

GRAPHITE.

For uses and statistics, see page 29.

GYPSUM.

For uses and statistics, see Plaster of Paris and Land Plaster, page 28.

LIMESTONE AND MARBLE.

For uses and statistics of limestone, see page 28; of marble, see pages 63 and 64.

MICA.

The micas are silicates possessing a remarkable basal cleavage which makes it possible to split them into exceedingly thin sheets. The plates of true micas are tough and elastic. There are several kinds of mica, but only the light colored ones, muscovite and phlogopite, have commercial value.

Uses.—When obtained in sheets of sufficient size, mica is used in stove and furnace doors, and in making chimneys for lamps and incandescent gas lights. Small sheets are used for purposes of insulation in electrical apparatus. Broken and scrap mica is used as a non-conducting covering for boilers and steam pipes, and, when finely ground, is used for giving lustre to wall paper, and as a lubricant. One kind of mica, lepidolite, is used for obtaining lithia, see page 37.

Statistics.—The domestic production of sheet mica (muscovite) in 1901 was 360,000 pounds, valued at nearly \$100,000. The supply came mostly from North Carolina, some from New Hampshire and South Dakota. The production of scrap mica was 2,000

tons valued at \$20,000. The importation of sheet mica in 1901 amounted to 1,700,000 pounds valued at \$335,000. The imported mica comes mostly from India, some from Canada, that from the latter country being chiefly phlogopite.

ORNAMENTAL OR DECORATIVE STONES.

There is an ever-growing demand for rocks or minerals of almost any kind which, when polished or worked into various shapes, may be used for ornamental purposes. The chief uses to which they are put are for making wainscotings for halls and offices, mantels, table tops, columns, vases and ornaments of endless variety. The materials generally used are as follows:

Marble, generally calcite, Ca CO_3 , white, mottled and variously colored.

Mexican Onyx.—This beautiful stone is a kind of translucent marble (calcite), formed by deposition from water. It generally is veined, clouded or mottled and shows delicate shades of color, varying from yellow, pink and green to pure white.

Verd-antique Marble, generally a mixture of white marble and green serpentine, often very decorative.

Granite, of great variety of color and size of grain.

Porphyry.—This is a name applied to rocks which contain regularly formed and comparatively large crystals imbedded in a ground-mass of finer grained rock material. Porphyries are of various kinds and colors, and, when polished, the contrast between the crystals and ground-mass may give pleasing and decorative effects.

Breccia.—This is a name given to material made up of irregular fragments of rocks and minerals, firmly cemented into a solid mass. When polished, the fragments of various kinds may give contrasts in color and structure which are effective and decorative.

Jade.—This is a compact, tough stone, generally of green or greenish-white color, especially prized by the Orientals. The material may be either nephrite, a variety of hornblende, or a rarer and more highly prized mineral, jadeite. Some oriental jade ornaments are of wonderful workmanship and almost inestimable value.

Serpentine, a compact mineral, generally of green color.

Quartz.—Transparent, colorless quartz (rock crystal), and various colored varieties of quartz, agate, jasper and chalcedony are often used.

Malachite, a basic carbonate of copper of bright green color.

Lapis-Lazuli, a silicate of ultramarine blue color.

Rhodonite, a silicate of manganese of rose-pink color.

Alabaster, a compact, even-grained variety of gypsum, often worked into ornaments resembling marble.

Satin Spar, a variety of fibrous gypsum, showing chatoyancy when polished.

Statistics.—The total value of the mineral products used for decorative purposes must be very great, but no statistics are available except for marble. The domestic production of marble in 1901 was valued at \$5,000,000, and it is estimated that about one-fourth of the product was used for interior and decorative work.

SANDSTONE.

For uses and statistics, see pages 45 and 46.

SLATE.

Slate is an argillaceous rock which may be split readily into slabs of nearly uniform thickness. Slate is used mostly for roofing, also for making billiard tables, mantels, floor tiles, stair treads and flagging. Ground slate is used as a pigment. The domestic production of roofing slate in 1902 was valued at over \$4,000,000, of manufactured products at about \$700,000, and of ground slate at \$40,000.

TALC AND SOAPSTONE.

Talc, $H_2 Mg_3 [Si O_3]_4$, is a soft, white or greenish-white mineral possessing a greasy feel. There is also an aluminium silicate, pyrophyllite, $H_2 Al_2 [Si O_3]_4$, which is practically identical with talc in its physical properties and is equally useful, although being rare it is not so well known as a commercial article.

Uses.—The uses of talc are quite varied: As powder or flour, talc is used in the manufacture of paper as a filler, and, when fibrous, it is claimed that it gives strength; it is used also as a base for fire-proof paints, as non-conducting covering for boilers and steam pipes, for making toilet powders, for dressing leather, and as a lubricant. Soapstone is manufactured into shapes suitable

for hearth stones, furnace linings, table tops, slate pencils, gas burner tips and a variety of articles.

Statistics.—In 1901 the production of ground, fibrous talc, suitable for paper making was 70,000 tons, valued at nearly \$500,000, the supply coming almost wholly from northern New York. Better grades of talc and soapstone, suitable for manufactured articles and flour talc, were obtained mostly in Virginia and North Carolina, the product being valued at about \$450,000.

PART III.

LISTS OF MINERALS ACCORDING TO GEOLOGICAL OCCURRENCE AND ASSOCIATION.

NOTE.—Although minerals occur associated with one another in almost endless variety, there are certain associations which are very often observed, and it is to call attention to these that the few remaining tables have been prepared.

PRINCIPAL ROCK MAKING MINERALS.

Quartz, Si O_2 .—In igneous and metamorphic rocks which are high in silica (granite, gneiss, mica schist), also in sedimentary rocks (conglomerate, sandstone, shale).

Potash-Feldspar, Orthoclase or Microcline, $\text{K Al Si}_3 \text{O}_8$.—In many igneous rocks, especially those which are high in silica (granite, gneiss, syenite).

Soda-Feldspar, Albite, $\text{Na Al Si}_3 \text{O}_8$. }

Lime-Feldspar, Anorthite, $\text{Ca Al}_2 \text{Si}_2 \text{O}_8$. }

Isomorphous mixtures of these two minerals are commonly known as the soda-lime, or plagioclase feldspars. The kinds generally recognized are *oligoclase*, *andesite* and *labradorite*, see page 21. The plagioclase feldspars are especially common in igneous rocks, and as a rule albite or oligoclase occurs in rocks, such as granite, which are high in silica, while labradorite or anorthite occurs in rocks, such as basalts, which are relatively low in silica.

Leucite, $\text{K Al} [\text{Si O}_3]_2$.—Found only in igneous rocks which are rich in potash and low in silica (leucite-basalt).

Elæolite or Nephelite, Na Al Si O_4 (approximately).—Found in igneous rocks (elæolite-syenite, nephelite-basalt) which are rich in soda and low in silica.

Sodalite, Haüynite, Noselite, Analcite.—Occasionally found in igneous rocks which are rich in soda.

Pyroxene or Augite.—A calcium-magnesium-iron silicate of variable composition (see page 18), very common in volcanic, but not often found in metamorphic rocks.

Ægirite or Acmite, $\text{Na Fe [Si O}_3\text{]}_2$.—A mineral related to pyroxene, of rather common occurrence in igneous rocks which are rich in soda and iron.

Enstatite, Bronzite, Hypersthene, Mg Si O_3 with isomorphous Fe Si O_3 .—Minerals of rather rare occurrence, generally found in basic igneous rocks (peridotites).

Hornblende or Amphibole.—A calcium-magnesium-iron silicate of variable composition, see page 18. Often found in plutonic and metamorphic rocks (granite, syenite, diorite, schists), but sparingly in volcanic rocks.

Mica, dark variety, Biolite, $(\text{H, K})_2 (\text{Mg, Fe})_2 \text{Al}_2 [\text{Si O}_4]_3$.—Common in plutonic and volcanic rocks (granite, syenite, diorite, andesite).

Mica, light variety, Muscovite, $\text{H}_2 \text{K Al}_3 [\text{Si O}_4]_3$.—Common in metamorphic rocks (mica schists), but rare in volcanic rocks.

Chrysolite, $(\text{Mg, Fe})_2 \text{Si O}_4$.—Generally found in volcanic rocks which are low in silica (basalt, peridotite).

Melilite, a mineral of uncertain composition, high in calcium and low in silica, occasionally observed in igneous rocks (melilite-basalt).

Allanite.—A mineral related to epidote, containing the rare-earth metals, Ce, La and Di, occasionally found in plutonic rocks (granite, gneiss).

Serpentine, $\text{H}_4 \text{Mg}_3 \text{Si}_2 \text{O}_9$.—Always a secondary mineral, resulting from the alteration of chrysolite or other magnesium silicates.

Chlorite or Clinocllore, $\text{H}_8 \text{Mg}_5 \text{Al}_2 \text{Si}_3 \text{O}_{18}$.—Always a secondary mineral, resulting from the alteration of magnesium silicates.

Kaolin, $\text{H}_4 \text{Al}_2 \text{Si}_2 \text{O}_9$.—Always a secondary mineral, generally resulting from the decomposition of feldspars. Kaolin is the basis of most clays.

Calcite, Ca C O_3 .—Occurs pure as marble, and more or less impure as the basis of limestone.

Dolomite, $\text{Ca Mg [Si O}_3\text{]}_2$.—Occurs pure as dolomite marble. Variable mixtures of Ca C O_3 and Mg C O_3 are known as dolomitic or magnesian limestone.

ACCESSORY MINERALS, COMMONLY FOUND IN ROCKS.

<i>Magnetite</i> , $\text{Fe}_3 \text{O}_4$.	} These iron minerals are commonly found in disseminated crystals or segregated masses in plutonic, volcanic and metamorphic rocks.
<i>Ilmenite</i> , Fe Ti O_3 .	
<i>Hematite</i> , $\text{Fe}_2 \text{O}_3$.	
<i>Pyrite</i> , Fe S_2 .	
<i>Pyrrhotite</i> , $\text{Fe}_{11} \text{S}_{12}$.	

<i>Apatite</i> , $\text{Ca}_4 [\text{Ca (F, Cl)}] [\text{P O}_4]_3$.	} Found in almost all plutonic and volcanic rocks, though generally in small quantities.
<i>Rutile</i> , Ti O_2 .	
<i>Titanite</i> , Ca Ti Si O_5 .	
<i>Zircon</i> , Zr Si O_4 .	

Garnet (almandite), $\text{Fe}_3 \text{Al}_2 [\text{Si O}_4]_3$.	} Found in metamorphic rocks (gneisses and schists).
Epidote,	
$\text{Ca}_2 [\text{Al . OH} (\text{Al, Fe})_2 [\text{Si O}_4]_3$.	
Staurolite,	
$(\text{Mg, Fe}) [\text{Al . OH} [\text{Al O}]_4 [\text{Si O}_4]_2$.	
Cyanite, $\text{Al}_2 \text{Si O}_5$.	

Iolite, Zoisite, Piedmontite, Scapolite or Wernerite, Andalusite and Sillimanite are minerals occasionally found in metamorphic rocks.

VEIN MINERALS.

1. In gold-bearing quartz veins.

Quartz, Si O_2 .	Chalcopyrite, Cu Fe S_2 .
Pyrite, Fe S_2 .	Arsenopyrite, Fe As S .

2. In veins carrying sulphide ores of silver, lead and zinc. The silver minerals are noted on page 47. The sulphides of lead and zinc are generally galena, Pb S , and sphalerite, Zn S or $(\text{Zn, Fe}) \text{S}$.

Quartz, Si O_2 .	Calcite, Ca C O_3 .
Pyrite, Fe S_2 .	Dolomite, $\text{Ca Mg [C O}_3]_2$.
Marcasite, Fe S_2 .	Siderite, Fe C O_3 .
Arsenopyrite, Fe As S .	Rhodochrosite, Mn C O_3 .
Chalcopyrite, Cu Fe S_2 .	Barite, Ba S O_4 .
Tetrahedrite, $\text{Cu}_8 (\text{Sb, As})_2 \text{S}_7$.	Fluorite, Ca F_2 .

3. Primary and secondary minerals of veins.

<i>Primary minerals.</i>	<i>Secondary minerals.</i>
Pyrite, Fe S_2 .	{ Limonite, $\text{Fe}_4 \text{O}_3 [\text{OH}]_6$.
Marcasite, Fe S_2 .	{ Melanterite, $\text{Fe SO}_4 \cdot 7 \text{H}_2\text{O}$.
	{ Native Copper.
	{ Malachite, $[\text{Cu} \cdot \text{OH}]_2 \text{CO}_3$.
Chalcopyrite, Cu Fe S_2 .	{ Azurite, $\text{Cu} [\text{Cu} \cdot \text{OH}]_2 [\text{CO}_3]_2$.
	{ Chrysocolla, $\text{Cu Si O}_3 \cdot 2 \text{H}_2\text{O} ?$
	{ Cuprite, $\text{Cu}_2 \text{O}$.
	{ Chalcantite, $\text{Cu SO}_4 \cdot 5 \text{H}_2\text{O}$.
	{ Cerussite, Pb CO_3 .
	{ Anglesite, Pb SO_4 .
Galena, Pb S .	{ Pyromorphite,
	$\text{Pb}_4 [\text{Pb Cl}] [\text{PO}_4]_3$.
	{ Wulfenite, Pb Mo O_4 .
	{ Smithsonite, Zn CO_3 .
Sphalerite, Zn S .	{ Calamine, $\text{H}_2 [\text{Zn}_2 \text{O}] \text{Si O}_4$.
	{ Goslarite, $\text{Zn SO}_4 \cdot 7 \text{H}_2\text{O}$.
Argentite, $\text{Ag}_2 \text{S}$, or other sulphide compounds of silver.	{ Native Silver.
	{ Cerargyrite, Ag Cl .
	{ Embolite, $\text{Ag} (\text{Cl}, \text{Br})$.
	{ Bromyrite, Ag Br .
Tellurides of gold.	Native Gold.
Feldspars.	Kaolin.

4. In pegmatite veins.

<i>Of common occurrence.</i>	<i>Of somewhat rare occurrence.</i>
Quartz.	Pyrite.
	Molybdenite.
Feldspar, { Orthoclase.	Lepidolite.
{ Microcline.	Spodumene.
{ Albite.	Triphylite.
Mica, { Muscovite.	Columbite.
{ Biotite.	Cassiterite.
Garnet, { Almandite.	Monazite.
{ Spessartite.	
Beryl.	
Tourmaline.	
Apatite.	

5. In veins or seams where pneumatolitic action has gone on; that is, where heated aqueous vapors, often containing boron and fluorine compounds, reacting under great pressure, have acted as mineralizing agents. Compare also minerals resulting from contact metamorphism, below.

Quartz.	Pyroxene.	Tourmaline.
Orthoclase.	Scapolite.	Datolite.
Microcline.	Muscovite.	Topaz.
Albite-oligoclase.	Biotite.	Apatite.
Tremolite.	Phlogopite.	Cassiterite.
Hornblende.	Titanite.	Fluorite.

MINERALS RESULTING FROM CONTACT METAMORPHISM.

When massive limestones are metamorphosed by contact with igneous rocks they are changed to crystalline limestone or marble, and the minerals given in the following table are very apt to be found along the zone of contact :

Graphite.	Tremolite.	Chondrodite.
Pyrrhotite.	Pyroxene.	Vesuvianite.
Spinel.	Phlogopite.	Scapolite.
Corundum.	Garnet, {	Grossularite. Tourmaline.
Wallastonite.		
		Andradite.

INDEX.

ABRASIVES.....	55	Arsenolite.....	3
Acmite.....	18	Arsenopyrite.....	12, 25
Adamite.....	15, 54	Asbestos.....	56
Ægirite.....	18, 48	Asphaltum.....	29
Æschynite.....	14	Astrophyllite.....	19, 52
Agate.....	58, 64	Atacamite.....	13, 31
Aguilarite.....	45	Augite.....	18
Aikinite.....	12	Aurichalcite.....	17, 54
Alabandite.....	5, 38	Autunite.....	15, 53
Alabaster.....	64	Awaruite.....	40
Albite.....	21, 48	Axinite.....	21, 26
Alexandrite, Chrysoberyl.....	59	Azurite.....	17, 31
Algodonite.....	22, 31		
Allanite.....	18, 30	BABINGTONITE.....	21
Alloclasite.....	12	Baddeleyite.....	54
Allophane.....	22	Barite.....	16, 25
Almandite.....	4, 34	Barium.....	25
Altaite.....	3, 36, 51	Barysilite.....	8, 36
Alum.....	5, 23, 24	Barytocalcite.....	17, 25
Aluminium.....	23	Bastnäsité.....	30, 32
Alunite.....	10, 23, 44	Baumhauerite.....	17
Amalgam.....	39, 47	Bauxite.....	22, 23
Amarantite.....	21	Berthierite.....	12
Amblygonite.....	21, 32, 37	Bertrandite.....	14, 25
Amethyst.....	58	Beryl.....	8, 25, 59
Amphibole.....	18, 37	Beryllium.....	25
Analcite.....	4, 48	Beryllonite.....	15, 25, 48
Anatase, Octahedrite.....	6	Berzelianite.....	3, 31, 45
Andalusite.....	14	Biotite.....	19, 44
Andesite.....	21	Bischofite.....	37
Andradite.....	4, 34	Bismuth.....	9, 26
Anglesite.....	16, 36	Bismuthinite.....	12, 26
Anhydrite.....	16, 27	Bismutite.....	26
Annabergite.....	20, 40	Bismutosphaerite.....	22, 26
Anorthite.....	21, 27	Bituminous Coal.....	29
Anthophyllite.....	13, 37	Bixbyite.....	4, 38
Anthophyllite-Asbestos.....	56	Blende, Sphalerite.....	5, 54
Anthracite Coal.....	29	Blödit.....	20, 37
Antimony.....	9, 24	Blue Vitriol.....	32
Apatite.....	9, 27, 32, 42	Bog Iron Ore, Limonite.....	22, 34
Apophyllite.....	6, 44	Boracite.....	5, 26, 37
Aquamarine.....	58	Borax.....	20, 26, 48
Aragonite.....	13, 27	Bornite.....	3, 31
Ardennite.....	14, 53	Boron.....	26
Argentite.....	3, 47	Bournonite.....	12
Argyrodite.....	3, 33, 47	Boytonite.....	21
Arsenic.....	9, 25	Brandtite.....	21

- Brass.....31
 Braunitz.....6, 38
 Breccia.....63
 Breithauptite.....9, 40
 Brewsterite.....19, 49
 Brimstone.....50
 Brochantite.....16, 31
 Bromine.....27
 Bromyrite.....27, 47
 Bronze.....32
 Bronzite.....13, 37
 Brookite.....13, 52
 Brucite.....10, 37
 Brushite.....20

CADMIUM.....27
 Caesium.....27
 Calamine.....14, 54
 Calaverite.....17, 33, 51
 Calcite.....10, 27
 Calcium.....27
 Calomel.....6, 39
 Cancrinite.....8, 48
 Canfieldite.....3, 33, 47, 51
 Carbonado, Diamond.....55
 Carborundum.....55
 Carnallite.....13, 37, 44
 Carnotite.....53
 Carpholite.....18
 Cassiterite.....6, 51
 Cat's eye, Chrysoberyl.....59
 Cattapleite.....54
 Celestite.....16, 49
 Cement.....56
 Cerargyrite.....3, 47
 Cerite.....14, 30
 Cerium.....30
 Cerussite.....13, 36
 Cervantite.....24
 Chabazite.....10
 Chalcantite.....21, 31
 Chalcedony.....64
 Chalcocite.....12, 31
 Chalcomenite.....20, 31, 45
 Chalcophanite.....10
 Chalcophyllite.....10, 31
 Chalcopyrite.....7, 31
 Chalcostibite.....12, 31
 Chalk.....28
 Childrenite.....15
 Chile Saltpeter.....41
 Chloanthite.....5, 25, 40
 Chlorine.....30
 Chlorite.....19, 37
 Chloritoid.....19
 Chondrodite.....18, 37
 Chrysoprase.....59
 Chromite.....3, 30
 Chromium.....30
 Chrysoberyl.....13, 25, 59
 Chrysocolla.....22, 31
 Chrysolite.....14, 37, 59
 Chrysotile-Asbestos.....56
 Cinnabar.....11, 39
 Clausthalite.....36, 45
 Clay.....56
 Clinocllore.....19
 Clinoclasite.....20, 31
 Clinohedrite.....18, 54
 Clinohumite.....18, 37
 Coal.....29
 Cobalt.....31
 Cobaltite.....5, 31
 Colemanite.....20, 26, 27
 Coloradoite.....39, 51
 Columbite.....14, 34
 Columbium.....31
 Copper.....2, 31
 Corundum.....10, 23, 55
 Cosalite.....12, 36
 Cotunnite.....13, 36
 Covellite.....8, 31
 Crocoite.....20, 30, 36
 Crookesite.....3, 45, 51
 Cryolite.....17, 23, 48
 Cuprite.....3, 31
 Cuprotungstite.....52
 Cyanite.....21, 23
 Cyndrite.....51

DANBURITE.....14, 26
 Darapskite.....48
 Datolite.....18, 26
 Dawsonite.....17, 48
 Decorative Stones.....63
 Descloizite.....15, 36, 53
 Deweylite.....22
 Diamond.....2, 29, 55, 59
 Diaspore.....13
 Didymium.....30
 Diopside.....18
 Dioptase.....11, 31

- Dolomite II, 27, 37, 67
 Domeykite 22, 31
 Dufrenite 15
 Dufrenoyseite 17, 36
 Dumortierite 14
 Durangite 20, 32, 48
 Durdenite 51
 Dyscrasite 47

EDINGTONITE 7
 Elæolite 66
 Embolite 3, 27, 47
 Emerald 59
 Emery 55
 Emmonsite 20, 51
 Emplectite 12, 26, 31
 Enargite 13, 25, 31
 Enstatite 13, 37
 Epidote 18
 Epsomite 16, 37
 Erbium 30
 Erythrite 20, 31
 Eucairite 45
 Euchroite 15, 31
 Euclase 18, 25
 Eucryptite 8, 37
 Eudialyte 10, 48, 54
 Eudidymite 18, 48
 Eulytite 5, 26
 Euxenite 14

FAIRFIELDITE 21
 Famatinite 12
 Fayalite 14, 34
 Feldspar 23, 44, 57, 66
 Fergusonite 7
 Ferro-chromium 30
 Ferro-manganese 38
 Ferro-molybdenum 39
 Ferro-nickel 40
 Ferro-silicon 45
 Ferro-titanium 52
 Ferro-tungsten 53
 Fiedlerite 8
 Flint 57
 Fluorine 32
 Fluorite 3, 27
 Flux 28
 Forsterite 14
 Franckeite 51
 Franklinite 3, 38, 54

 Freieslebenite 17
 Fuller's Earth 57

GADOLINITE 18, 25, 30
 Gahnite 3, 54
 Galena 3, 36
 Galenobismuthite 12
 Gallium 33
 Ganomalite 6, 36
 Garnet 4, 56, 59
 Garnierite 22, 40
 Gay-Lussite 17, 27, 48
 Gem Minerals 58
 Genthite 22, 40
 Gerhardite 15, 31
 Geocronite 12
 Germanium 33
 German Silver 32
 Gersdorffite 5, 25, 40
 Gibbsite 17, 23
 Glauberite 20, 27, 48
 Glaucocroite 14, 38
 Glauco-dot 12, 31
 Glaucophane 18, 48
 Gmelinite 10
 Göthite 13, 34
 Gold 2, 33
 Goslarite 16, 54
 Granite 62, 63
 Graphite 9, 29
 Greenockite 9, 27
 Grossularite 4
 Guanajuatite 45
 Gummite 53
 Gypsum 20, 27

HALITE 3, 48
 Hambergite 15
 Hamlinite 10, 49
 Hanksite 8, 48
 Hardystonite 6
 Harmotome 19, 25
 Hauerite 5, 38
 Hausmannite 6, 38
 Häüynite 4, 48
 Helvite 5, 25, 38
 Hematite 10, 34
 Herderite 19, 25, 32
 Hessite 3, 47, 51
 Heulandite 19
 Hiddenite, Spodumene 61

- Homilite.....18
 Hopeite.....54
 Hornblende.....18
 Howlite.....15
 Hübnerite.....20, 38, 52
 Humite.....14, 18, 37
 Hyalophane.....18, 25
 Hydrogen.....33
 Hydromagnesite.....17, 37
 Hydrozincite.....22, 54
 Hypersthene.....13

ILMENITE.....11, 34, 52
 Ilvaite.....14, 34
 Indium.....33
 Inesite.....21, 38
 Infusorial Earth.....46
 Iodine.....34
 Iodyrite.....9, 34, 47
 Iolite.....13
 Iridium.....34
 Iridosmine.....8
 Iron.....2, 34

JADE.....63
 Jadeite.....18, 48, 63
 Jamesonite.....12, 36
 Jarosite.....10, 34, 44
 Jasper.....60, 64
 Jordanite.....17
 Josephinite.....40

KAINITE.....20, 37, 44
 Kalinite.....5, 23, 44
 Kaolin.....19, 23, 56
 Kentrolite.....14, 36
 Kermesite.....24
 Krennerite.....12, 33, 51

LABRADORITE.....21
 Land Plaster.....28
 Langbeinite.....44
 Lansfordite.....21, 37
 Lanthanite.....13, 30
 Lanthanum.....30
 Lapis-Lazuli.....60, 64
 Laumontite.....19
 Lauterite.....34
 Lazulite.....20, 23
 Lazurite.....4, 48, 60
 Lead.....36
 Leadhillite.....17
 Lepidolite.....19, 32, 37
 Lepidomelane.....19
 Leucite.....4, 23, 44
 Leucophanite.....13, 25
 Libethenite.....15, 31
 Lime.....28
 Limestone.....27
 Limonite.....22, 34
 Linarite.....20
 Linnaeite.....3, 31
 Lithiophilite.....15, 37, 38
 Lithium.....37
 Lölingite.....12, 25
 Lorandite.....51
 Ludwigite.....15

MAGNESITE.....10, 37
 Magnesium.....37
 Magnetite.....3, 34
 Malachite.....17, 31, 64
 Manganese.....38
 Manganite.....13, 38
 Manganosite.....3, 38
 Marble.....27, 63
 Marcasite.....12, 34
 Margarite.....19
 Marshite.....5, 34
 Massicot.....36
 Matildite.....12, 47
 Matlockite.....6, 36
 Melaconite.....31
 Melanotekite.....14, 36
 Melanterite.....20, 34
 Melonite.....40, 51
 Meneghinite.....12, 36
 Mercury.....39
 Metacumabarite.....39
 Mexican Onyx.....63
 Miargyrite.....17, 47
 Mica.....23, 37, 62
 Microcline.....21, 44, 66
 Microlite.....4
 Miersite.....5, 34
 Millerite.....9, 40
 Mimetite.....9, 25, 36
 Mineral Paint.....35
 Minium.....36
 Mirabilite.....20, 48
 Molybdenite.....8, 39
 Molybdenum.....39

- Molybdenite 39
 Monazite 19, 30
 Montanite 51
 Monticellite 14, 37
 Moonstone 60
 Morenosite 16, 40
 Muscovite 19, 44

 NAGYAGITE 51
 Nantokite 3
 Nasonite 6, 36
 Natrojarosite 10, 48
 Natrolite 14, 48
 Natron 17, 48
 Natrophilite 15, 48
 Natural Gas 29
 Naumannite 45
 Nephelite 8, 23, 48
 Nephrite, Jade 63
 Nesquehonite 13, 37
 Niccolite 9, 25, 40
 Nickel 40
 Niobium 40
 Niter 15
 Nitrogen 41
 Nordenskiöldine 51
 Northupite 4, 48
 Noselite 48
 Noumeaite 22, 40
 Novaculite 46

 OCTAHEDRITE 6, 52
 Oligoclase 21
 Olivenite 15, 25, 31
 Olivine 14
 Onofrite 5, 39, 45
 Opal 22
 Ornamental Stones 63
 Orpiment 17
 Orthoclase 18, 44, 66
 Osmium 41
 Oxygen 42
 Ozokerite 29

 PACHNOLITE 17, 48
 Palladium 42
 Paragonite 19, 48
 Parisite 8, 30, 32
 Pearceite 17, 47
 Pectolite 18, 48
 Penninite 10
 Pentlandite 3, 40
 Percylite 3, 36
 Periclase 3, 37
 Peridot 60
 Peristerite, Moonstone 60
 Perovskite 4, 27, 52
 Petalite 18, 37
 Petroleum 29
 Petzite 3, 33, 47, 51
 Pharmacosiderite 5
 Phenacite 11, 25
 Phillipsite 19
 Phlogopite 19
 Phosgenite 6, 36
 Phosphate Rock 42
 Phosphorus 42
 Piedmontite 18, 38
 Pirssonite 13, 48
 Pitchblende 53
 Plagionite 17
 Plaster of Paris 28
 Platinum 2, 43
 Plattnerite 6, 36
 Plumbojarosite 10
 Polianite 6, 38
 Pollucite 4, 27
 Polyargyrite 47
 Polybasite 17, 47
 Polycrase 14
 Polyhalite 20, 44
 Polymignite 14, 54
 Porphyry 63
 Potassium 44
 Powellite 39
 Precious Stones 58
 Prehnite 14
 Prolectite 18
 Proustite 9, 25, 47
 Pseudobrookite 52
 Psilomelane 22, 38
 Pucherite 15, 26, 53
 Pumice 56
 Pyrargyrite 9, 24, 47
 Pyrite 5, 34, 50
 Pyrochlore 4
 Pyrochroite 10, 38
 Pyrolusite 13, 38
 Pyromorphite 9, 36
 Pyrope 4
 Pyrophyllite 19, 23
 Pyrophyllite, Talc 64

- Pyrosmalite.....8
 Pyroxene.....18, 37, 60
 Pyrrhotite.....8, 34, 40

 QUARTZ.....11, 46, 60, 64
 Quartzite.....46
 Quicksilver.....39

 RALSTONITE.....3
 Rammelsbergite.....12, 40
 Raspite.....52
 Realgar.....17
 Reddingite.....15
 Reinite.....52
 Rhodium.....45
 Rhodochrosite.....10, 38
 Rhodonite.....21, 38, 64
 Rickardite.....31, 51
 Rock Making Minerals.....66
 Roscoelite.....19, 53
 Roselite.....21
 Rubellite, Tourmaline.....61
 Rubidium.....45
 Ruby.....61
 Ruby-Copper, Cuprite.....3, 31
 Ruby-Silver, Proustite.....9, 47
 Ruthenium.....45
 Rutile.....6, 52

 SALT, Halite.....3, 48
 Safflorite.....12
 Samarskite.....14
 Sandstone.....46
 Sapphire.....61
 Sartorite.....12, 36
 Sassolite.....21, 26
 Satin Spar.....64
 Scapolite.....7, 48
 Scheelite.....7, 27, 52
 Schoenite.....20, 37, 44
 Schorlomite.....52
 Scolecite.....19
 Scorodite.....15, 25, 34
 Selenium.....45
 Selen-Tellurium.....45, 51
 Sellaite.....37
 Senarmontite.....3, 24
 Serpentine.....19, 37, 63
 Serpentine-Asbestos.....56
 Seybertite.....19
 Siderite.....10, 34

 Silicon.....45
 Sillimanite.....14
 Silver.....2, 47
 Slate.....64
 Smaltite.....5, 25, 31
 Smithsonite.....10, 54
 Soapstone.....64
 Soda-Niter.....10, 41, 48
 Sodalite.....4, 48
 Spangolite.....10, 15
 Spelter, Zinc.....54
 Sperrylite.....5, 43
 Spessartite.....4, 38
 Sphalerite.....5, 54
 Spiegeleisen.....38
 Spinel.....3, 37, 61
 Spodumene.....18, 37, 61
 Stannite.....6, 51
 Staurolite.....14
 Stephanite.....12, 47
 Stibiconite.....24
 Stibnite.....12, 24
 Stilbite.....19
 Stolzite.....7, 36, 52
 Strengite.....15
 Stromeyerite.....12, 31, 47
 Strontianite.....13, 49
 Struvite.....15
 Sulphohalite.....4, 48
 Sulphur.....12, 50
 Sussexite.....15, 38
 Sylvanite.....17, 33, 47, 51
 Sylvite.....3, 44
 Syngenite.....20

 TACHYDRITE.....37
 Talc.....19, 37, 64
 Tantalum.....50
 Tapiolite.....6
 Tellurite.....51
 Tellurium.....9, 51
 Tennantite.....5, 31
 Tenorite.....31
 Tephroite.....14, 38
 Tetradymite.....9, 26, 51
 Tetrahedrite.....5, 24, 31
 Thallium.....51
 Thaumassite.....8
 Thenardite.....16, 48
 Thermonatrite.....48
 Thomsenolite.....17, 48

- Thomsonite.....14
 Thorite.....6, 30
 Thorium.....30, 51
 Tiemannite.....5, 39, 45
 Tin.....51
 Titanic Iron.....52
 Titanite.....19, 27, 52
 Titanium.....52
 Topaz.....14, 24, 32, 61
 Torbernite.....6, 53
 Tourmaline.....10, 26, 61
 Tremolite.....18
 Tremolite-Asbestos.....56
 Tridymite.....8
 Triphylite.....15, 34, 37
 Triplite.....20, 32, 38
 Triploidite.....20, 38
 Trona.....17, 48
 Tungsten.....52
 Tungstite.....52
 Turgite.....22, 34
 Turquoise.....22, 23, 61
 Tysonite.....8, 30

 ULEXITE.....26, 48
 Ullmannite.....5, 40
 Umangite.....45
 Uraninite.....4, 53
 Uranium.....53
 Uranophane.....53
 Uranothalite.....53
 Useful Minerals.....55
 Uvarovite.....4, 30

 VALENTINITE.....13, 24
 Vanadinite.....9, 36, 53
 Vanadium.....53
 Vein Minerals.....68
 Verd-antique Marble.....63

 Vermiculite.....19
 Vesuvianite.....6
 Vivianite.....20, 34
 Volborthite.....53

 WAGNERITE.....20, 32, 37
 Warwickite.....15
 Wavellite.....15, 23
 Wellsite.....19
 Wernerite.....7, 48
 Whewellite.....20
 Whitneyite.....22, 31
 Willemite.....11, 54
 Witherite.....13, 25
 Wittichenite.....12
 Wöhlerite.....54
 Wolfachite.....12
 Wolframite.....20, 34, 52
 Wollastonite.....18, 27
 Wulfenite.....7, 36, 39
 Wurtzite.....9, 54

 XANTHOSIDERITE.....22
 Xenotime.....6, 30

 YTTRIUM.....30, 54
 Yttrotantalite.....14

 ZARATITE.....22, 40
 Zeolites.....23
 Zeunerite.....6, 53
 Zinc.....54
 Zincite.....9, 54
 Zinkenite.....12, 36
 Zircon.....6, 54, 61
 Zirconium.....54
 Zoisite.....14
 Zunyite.....5, 32

